



The pyrolysis of naphthacene
by John Charles Philip

A thesis submitted to the Graduate Faculty in partial fulfillment of the requirements for the degree of
MASTER OF SCIENCE in CHEMICAL ENGINEERING

Montana State University

© Copyright by John Charles Philip (1967)

Abstract:

The pyrolysis of naphthacene was studied in a Thermogravi-metric Analysis (TGA) apparatus in order to obtain information which might be useful in the manufacture of commercial pyrolytic graphite.

During the pyrolysis runs, data was obtained concerning amount of weight loss, temperature, and rate of evolution of the gases produced by pyrolysis. Following the runs, the products were analyzed. The final temperature of all runs used for quantitative purposes was 625-630°C. The results of the product analysis were used to form a stoichiometric equation for the overall reaction of naphthacene.

Four compounds and unreacted naphthacene were found to be present in the condensate. One of these was 5,12-dihydronaphthacene. The other compounds appear to be two oxygenated compounds and one compound that maybe the result of further reaction of dihydronaphthacene.

222

THE PYROLYSIS OF NAPHTHACENE

by

JOHN CHARLES PHILIP

A thesis submitted to the Graduate Faculty in partial
fulfillment of the requirements for the degree

of

MASTER OF SCIENCE

in

CHEMICAL ENGINEERING

Approved:

Lloyd B. King

Head, Major Department

Robert L. Nickelson

Chairman, Examining Committee

A. J. Goering

Graduate Dean

MONTANA STATE UNIVERSITY
Bozeman, Montana

December, 1967

Acknowledgement

The author wishes to thank the staff of the Chemical Engineering Department at Montana State University for the help which they gave him during the course of this project. Special thanks go to Dr. Robert L. Nickelson, who served as thesis adviser, and to Dr. Michael Schaer, who did a great deal of the work involved in the building of the chromatograph used to analyze the reaction gases and who also did most of the troubleshooting when things went wrong with the chromatograph used to analyze the condensate.

He also wishes to thank Dr. Robert Currie, who built the TGA apparatus which was used in the experimental work; Mr. William War, who also helped with the building of the chromatograph used to analyze the gaseous products; Dr. Graeme Baker, who provided assistance with the interpretation of spectra obtained during the analytical work; and Dr. Joseph Kiovsky, for his information about industrial preparation of pyrolytic graphite.

For their financial aid during the course of this project, the author wishes to thank the Continental Oil Company and the National Aeronautics and Space Administration.

Finally, he would like to thank his wife, Anita, for her assistance in getting his experimental data onto cards for computer input.

Table of Contents

	Page
List of Tables	v
List of Figures	vi
Abstract	vii
Introduction	1
Equipment	6
Experimental and Analytical Procedures	9
Results and Discussion	15
Conclusions	31
Appendix	33
Literature Cited	89

List of Tables

	Page
Table I	Compounds Involved in this Work 34
Table II	Points in Calibration Curves 35
Table III	Program to Read Calibration Curves 36
Table IV	Interpolation Subroutine 38
Table V	Program for Integration of Gas Evolution Data 40
Table VI	Program to Graph Tables VII-X 42
Table VII	Ex-NA-7 44
Table VIII	Ex-NA-8 51
Table IX	Ex-NA-10 58
Table X	Ex-NA-11 65
Table XI	Results of Individual Runs 72
Table XII	Products of the Pyrolysis of One Mole of Naphthacene 73
Table XIII	Variable Names in the Computer Programs . . . 74

List of Figures

	Page
Figure 1 Thermogravimetric Analysis Apparatus	75
Figure 2 Equipment Modifications and Product Locations	76
Figure 3 Ex-NA-7 Results	77
Figure 4 Ex-NA-8 Results	78
Figure 5 Ex-NA-10 Results	79
Figure 6 Ex-NA-11 Results	80
Figure 7 Chromatogram of Gaseous Products	81
Figure 8 Condensate Chromatogram	82
Figure 9 Infrared Spectrum of Compound II	83
Figure 10 Infrared Spectrum of Compound I	84
Figure 11 Ultraviolet Spectrum of Compound I	85
Figure 12 Infrared Spectrum of Compound III	86
Figure 13 Infrared Spectrum of Compound IV	87
Figure 14 Ultraviolet Spectra of Compounds III and IV in Ethanol	88

Abstract

The pyrolysis of naphthacene was studied in a Thermogravimetric Analysis (TGA) apparatus in order to obtain information which might be useful in the manufacture of commercial pyrolytic graphite.

During the pyrolysis runs, data was obtained concerning amount of weight loss, temperature, and rate of evolution of the gases produced by pyrolysis. Following the runs, the products were analyzed. The final temperature of all runs used for quantitative purposes was 625-630°C. The results of the product analysis were used to form a stoichiometric equation for the overall reaction of naphthacene.

Four compounds and unreacted naphthacene were found to be present in the condensate. One of these was 5,12-dihydronaphthacene. The other compounds appear to be two oxygenated compounds and one compound that may be the result of further reaction of dihydronaphthacene.

Introduction

Pyrolysis or thermal decomposition is the process of breaking chemical bonds by means of thermal energy. Unless pyrolysis occurs in the presence of catalysts, it is known to proceed by a free radical mechanism and the products of pyrolysis may be predicted to some extent by means of the application of the knowledge of free radical chemistry.

The manufacture of pyrolytic graphite involves the pyrolysis of a feed stock that is primarily aromatic in character. The components of this feed that end up in the finished graphite are primarily polynuclear aromatic hydrocarbons or compounds which are capable of undergoing reactions which form this class of compounds. Lighter compounds will distill off during the process of heating the feed to the temperatures required to form graphite. Other classes of compounds besides polynuclear aromatic hydrocarbons can undergo pyrolysis and yield a high molecular weight carbonaceous residue, but ordinarily this residue will not yield a high-oriented graphite (1). There are two primary considerations which determine whether a given compound will give a well-oriented graphite. The first of these involves the structure of the original molecule. If the starting compound is not planar or has a great deal of steric crowding, it is not likely to form a well-oriented graphite. The second involves the melting point of the starting material. Brooks and Taylor found that well-oriented graphites did not result unless fusion of the starting compound occurred prior to the reactions producing graphite-like structures (2). For

these same reasons, if the mechanism of thermal decomposition for a molecule involves intermediates with the characteristics mentioned above, the compound is likely to form a graphite that is not well-oriented.

Compounds which form graphites react in the following manner: First, an aryl radical is formed by the rupturing of a carbon-hydrogen bond or by the attack of a radical on an aryl hydrogen. A diaryl molecule can then form in one of two ways. The first and least probable way is by combination of two aryl radicals. A more likely mechanism is the addition of an aryl radical to an aromatic molecule followed by the removal of hydrogen to give a diaromatic system. In order to get compounds with structures similar to that of graphite, cyclodehydrogenation takes place to give a more completely aromatic system. For example, in the tar formed by flow pyrolysis of anthracene at 700°C are 9,9'-bianthryl, 1,2:11,12-dibenzoperylene, and other compounds which could be formed by cyclodehydrogenation of the above or of compounds formed by some of the other possible radicals of anthracene (3). The structures of these compounds are shown in Table I.

The commercial manufacture of pyrolytic graphite involves a two-step process. During the first step of the process, a coke is formed by heating the feed stock slowly to approximately 800°F. During this heating period, the temperature may be allowed to level off at various intermediate points in order to help to remove impurities

which may be present in the feed. After the temperature reaches its final value, it is kept there for a predetermined length of time. The resultant coke is then made into electrodes and heated in an electric furnace to the 2500°C temperatures which are required in order to produce graphitic products (4).

At the present time it is not possible to tell in advance what the quality of the final graphite resulting from a given coker feed stock will be without taking a sample of the feed and actually making graphite from it. It would be desirable to be able to obtain enough information from the initial coking process to be able to tell what the ultimate graphite quality from the feed would be (4).

Most of the literature oriented toward the preparation of graphite from polynuclear aromatic hydrocarbons is based on work done by the Union Carbide Corporation for the Air Force Materials Laboratory. They took a large number of compounds and heated them to 750°C in a Differential Thermal Analysis (DTA) unit and classified these compounds as either thermally "reactive" or "unreactive", depending on whether they gave a measurable amount of carbonaceous residue at the end of the DTA run. These runs were made at atmospheric pressure (5). Out of those compounds which were found to be "reactive", they selected approximately 100 compounds to convert to graphite by heating to 3000°C. The orientation of the resultant graphite was then studied by means of x-ray diffraction. The 002 lattice spacing was selected to reflect the orientation of the graphite. The lower the value of this spacing, the

better is the orientation of the graphite (1). Graphites with a value for this spacing greater than 3.366 Angstroms are poorly oriented (1).

The purpose of this study was to study the reactions of compounds similar to those which would be found in coker feed stocks used in the manufacture of pyrolytic graphite with the hope that the information resulting might be useful in coker design and also might provide a useful way of testing a coker feed stock in order to predict how good a graphite it would make.

Two compounds were selected for this study: 1,2,5,6-dibenzanthracene and naphthacene. The first compound was selected because information available in the literature (6) indicated that the only gaseous products present in significant quantities after pyrolysis of this compound in a sealed glass ampoule were hydrogen and methane. This would make analysis and subsequent determination of kinetic information much simpler than if more gaseous products resulted. The chief disadvantage of this compound is that we wanted to know how well-ordered a graphite would result from the compounds selected and dibenzanthracene was classified in the work done by Union Carbide as thermally "unreactive" (5). DTA of this compound showed a boiling point at 520°C.

In the equipment used for this study, it was possible to obtain a 35% yield of carbonaceous residue based on original sample size when the pyrolysis of dibenzanthracene was being investigated. In the DTA work done by Union Carbide, the heating rate used was ten degrees per

Equipment

A drawing of the equipment used to conduct the pyrolysis is shown in Figure 1. Basically, it consists of a stainless steel reaction chamber which is suspended from a continuous recording balance. The piece of tubing from which the reactor is suspended is also the thermowell for measurement of reactor temperature. The balance is the same one which R. A. Currie built for his study on the pyrolysis of acenaphthylene and bifulorenyl (7). Figure 1 shows the equipment as it appeared while Currie was doing his work. Figure 2 shows some of the modifications which were necessary in order to make the equipment perform satisfactorily for naphthacene. Comparison of Figures 1 and 2 shows that the design of the cap which fits over the heated zone was changed. This was done for two reasons. It was felt that the amount of oxygen getting to the reacting materials would be decreased sharply by increasing the length of the path required for its diffusion. The primary reason, however, for the change in design was to allow the installation of an additional heater. The purpose of this heater was to prevent the condensation of the heavier products which distilled off during the runs. In the early runs which were made on naphthacene, heavy solid products would condense on the thermowell and along the tube leading from the condenser to the reactor. This would result in the fouling of the balance. The heater was installed in order to raise the temperature of the gas coming in contact with these products to a value sufficiently high to prevent condensation from occurring until they reached the condenser region. The heater consisted of nichrome wire with ceramic bead insulation wrapped around this cap

and the beginning of the nipple leading away from the cap.

In addition to the equipment shown in Figures 1 and 2, there is a chromatograph built especially for this project hooked up to the outlet in order to analyze for the non-condensable gases produced. The chromatograph, which contains a thermal conductivity detector, uses a 1/4-inch diameter column that is packed with Porapak Q 100/120 to separate and analyze the gaseous products of naphthacene pyrolysis. This column is six feet six inches in length. Immediately before the chromatograph is located a glass wool filter to remove the last of the solid products from the gas stream and a tube of drierite to remove any water that may be contained in the stream. The carrier gas used in the chromatograph was nitrogen at 65 cc/min. The column temperature was 118.5°C. Nitrogen was used because helium, which is the preferred gas for methane and ethane chromatography, is very poor for hydrogen. Nitrogen is also inexpensive enough to use as a purge for the system.

The chromatograph was provided with an automatic sampling valve in order to have exactly the same sample size at every injection. This was very important since it was necessary to have information about absolute concentration of the individual components of the gas being analyzed. This uniformity in sample size can not ordinarily be achieved with a syringe.

The last piece of equipment used during the reaction was a positive displacement pump which was used to pull the gases leaving the condenser through the sample valve at a constant rate. It did this by

pumping water out of a sealed bottle which was connected to the outlet end of the sample valve at the required rate.

The remainder of the equipment is that which was used for analysis and identification of the products. An Aerograph 660 gas chromatograph equipped with a flame ionization detector was used to analyze the condensate. The column that was used was a 1/8-inch diameter, twenty-five foot column packed with 5% SE-30 on 50/60 mesh Anakrom ABS. The carrier gas was nitrogen at 25 cc/min. The column temperature was 242°C.

The infrared spectra used to identify one of the products and to aid in the characterization of one of the other products in the condensate were run in a Beckman IR-4 Infrared Spectrophotometer. The infrared spectra of another condensate fraction were run by Huffman Laboratories in Wheatridge, Colorado.

Ultraviolet spectra were run in a Beckman DK-2 Ultraviolet and Visible Spectrophotometer.

Preparative Chromatography was done in an Aerograph 200 gas chromatograph in a 1/4-inch column, fifteen feet long, packed with the same material as that used to analyze the condensate using hydrogen as carrier gas at 30 cc/min. The column temperature was 250°C.

Experimental and Analytical Procedures

The sample size used in the pyrolysis runs under discussion here was between 0.9 and 1.1 grams. Prior to the beginning of the runs, the nitrogen supply to the reactor and that used to provide a continuous purge to the reaction chamber shown in Figure 1 was turned on. During the progress of the run, the rate of supply of nitrogen was kept slightly higher than the rate of its removal through the sample valve in order to help to cut down on the amount of oxygen entering the system.

On the day of the run, samples of the calibration gas were run through the sample valve at approximately the same rate at which the reaction gases would be pulled through the valve during the run in order to check the calibration curve and to provide a means of correction for the normal variation in atmospheric pressure that occurs.

The calculation of gas evolution rates was done by using the peak heights shown on the reaction-monitoring gas chromatograph. A calibration curve was made using a calibration gas purchased from the Matheson Company which contained 5.27 mol% hydrogen, 5.33% methane, and 5.43% ethane in nitrogen. The calibration curve was made by injecting samples of $\frac{1}{4}$, 1, 2, and 4 cc through the sampling valve at approximately the same rate at which the gases are pulled through it during the pyrolysis runs. This gas contains hydrogen, methane, and ethane at approximately the same concentrations in which they appear in the gaseous product mixture. Since the sample loop is not connected to carrier gas pressure until the moment of injection and the sample loop is outside

the chromatograph and far enough from the reaction area for the gases to cool to room temperature, the calibration curve was based on ambient temperature and pressure.

Twenty-five degrees centigrade was assumed as the temperature and the pressure was measured prior to every run in order to make corrections on the calibration curve. Since the calibration curve was based on a flow rate through the sample valve of 65 cc/min, it was necessary to correct for deviations from this value which occurred during the runs. The variations in ambient temperature were not corrected for since the original calibration curve was made using the assumption that sample valve temperature was the same as that in the chromatograph. The 4-cc sample loop was used during all of the runs. The gas evolution rate could then be calculated by means of the following equation:

$$\frac{\text{moles}}{\text{sample}} \times \text{flow rate} = \frac{\text{moles}}{\text{min}}$$

In this equation the flow rate must be expressed as the number of 4-cc samples per minute. The points used to make the calibration curve are shown in Table II. A computer program which was used to read the calibration curves is shown in Table III. The subroutine which will do the necessary interpolations is shown in Table IV. This subroutine takes the four points on the calibration curve nearest to the desired value and fits a fourth order polynomial through them and then calculates the desired intermediate value. The input to the curve reading program

includes calibration curve data taken from a graph which was drawn of the calibration for approximately every five units of peak height. It also includes the values of peak height for the gases taken during the run being analyzed.

Another program was written to integrate the gas evolution rate curves in order to obtain stoichiometric coefficients for the gases.

It is shown in Table V that the output of this program was time, temperature, fraction of original sample corresponding to the amount of weight lost since the beginning of the run, total amount of gas evolved per gram of sample, and per gram of material remaining in the reactor. Gas evolution rate was expressed in both of these ways in order to decide which of the two values to present in the form of graphs. The values in the individual runs are affected by so many other variables other than temperature, such as the rate of temperature increase at the time at which the sample is taken, that the rates at a given temperature do not agree very well with those from other runs, no matter which basis is chosen as a means of expression of the rate. The rate per gram of sample was chosen as the expression to present. The rate per gram remaining in the reactor can easily be calculated from the other. The output of this program also provided the input to the program shown in Table VI which made the graphs shown in Figures 3-6.

During the progress of the runs, an attempt was made to keep the rate of temperature increase as close as possible to 1.67 degrees Centigrade per minute in order to get a better comparison between the re-

sults of the different runs. The rate of temperature increase prior to the temperature at which naphthacene melts (357°C) was found to be not critical since there does not appear to be any significant amount of reaction prior to that temperature.

After melting had occurred, the gas was sampled every five minutes until propane began to be evolved. It was then necessary to wait six minutes in order to allow the pen to get back to the baseline before injecting a new sample.

At the time of sample injection, a record was made of pumping rate. For the compounds which were used for this study, this was necessary because at the time during the run during which large quantities of condensate were coming off, ($420-500^{\circ}\text{C}$) enough condensate would collect in the tubing leading to the chromatograph to cause a great increase in resistance to flow. Since the calibration curve which gives gas evolution rate from the chromatograph peak height is based on a constant flow rate of 65 cc/min, any significant deviation from this flow rate must be corrected for.

The complete runs were terminated after the temperature of the reactor had remained constant at 625°C to 635°C for 15 minutes. The interrupted runs were terminated either after 15 minutes at some designated temperature if weight loss had not yet begun, or when the reactor had reached approximately constant weight.

After the runs had been completed, the final weight of the reactor was recorded and the carbonaceous residue was scraped out. This residue was extracted for 24 hours in a Soxhlet Extraction Apparatus to measure the amount of benzene-soluble material present in the residue.

The condensate was first separated manually into two fractions: unreacted naphthacene and other condensate. It was necessary to make this separation before chromatography because the chromatograph column used would not resolve naphthacene and some of the other compounds present in the condensate. This separation could be made with little difficulty, provided that enough condensate was present, since an interface forms in the condenser between naphthacene, which is red, and one of the other compounds, which forms yellow crystals. The fraction from which the naphthacene had been removed was then analyzed in the chromatograph.

Additional work was done on the condensate from some of the runs in order to identify some of the products.

The most important thing that was done was manual preparative chromatography, which allowed condensate samples to be separated into fractions containing some of the compounds making up the condensate in high purity. Some of these were sent to Huffman Laboratories for analysis of molecular weight and carbon and hydrogen content. Infrared and ultraviolet spectra and melting point were taken with equipment available on this campus. The infrared spectra that were obtained

were run in approximately 1% concentration in KBr micropellets in a Beckman IR-4 Infrared Spectrophotometer. The ultraviolet spectra were run in an approximately saturated solution in ethanol in a Beckman DK-2 Spectrophotometer.

Results and Discussion

A total of 13 pyrolysis runs were made on naphthacene. Eleven of these were terminated at 625-630°C. The last two runs were made to intermediate temperatures in order to obtain information about when different reactions were occurring. For the complete runs (termination temperature 625-630°C), the supplier of the naphthacene was K & K Chemical Company. The supplier for the interrupted runs (those terminated at intermediate temperatures), was the Distillation Products Division of the Eastman Kodak Company. It was not possible to use the same supplier for all of the runs because K & K ran out of naphthacene shortly before the time that the naphthacene required for the interrupted runs was ordered. Only the last four of the complete runs will be discussed here since information obtained in these last four runs indicated that the results of the first six runs was not truly representative of the reaction of naphthacene at the measured temperatures of reaction.

The main problem which had to be solved in order to get data representing a true picture of the reactions occurring at the indicated temperatures was getting the high molecular weight vaporizable compounds produced by the pyrolysis into the condenser region without condensing prematurely or undergoing further reaction. When the equipment was set up as shown in Figure 1, the temperature of the gases entering the condenser region was only 140°C, well below the melting points of all but one of the compounds which were isolated during this study. This resulted in the condensation of the solid products as soon

as they left the hot reaction zone. The products would then collect on top of the reactor, on the walls of the passageway leading to the condenser, and on the outside of the thermowell. Eventually enough of them would collect to foul the balance and no meaningful weight loss data could be obtained. This problem was first solved by putting an additional resistance heater around the cap, as shown in Figure 2. With this heater it was possible to raise the gas temperature to 318°C , which was sufficient to get all of the solid products at least as far as the nipple leading away from the cap. Unfortunately, the surface temperature of the cap necessary to produce this gas temperature introduced some materials problems. This temperature was high enough to produce scale on the surface which was difficult to keep from dropping into the product when cleaning the apparatus at the end of the run. Evidence was also obtained that the cap was hot enough so that the unreacted naphthacene which distilled off and collected in the nipple continued to react and give off products. The final solution came from the installation of another preheater external to the apparatus. This made it possible to heat the gases entering the condenser to 270°C without making the nipple region hot enough to cause the continuation of pyrolysis there.

The information obtained during the complete runs is shown in Figures 3-6. The same information is presented in tabular form in Tables VII-X. The gas evolution rates which were obtained directly from the chromatograms made during the runs are underlined.

On a qualitative basis, the results obtained during the runs are quite similar. They all show maxima in hydrogen evolution rate at 425-435°C and a smaller maximum toward the end of the run near where the temperature began to level off. The curves for methane show maxima at 470-485°C and one run (Ex-NA-7) shows another maximum at 518°C. (Note that the value of moles of gas/min. gm of sample at the first maximum for this run was considerably lower than that for the other runs. All of the runs show maxima in ethane evolution rates at 460-485°C. In addition to the results shown on these graphs, there is a maximum evolution rate for propane at 460-475°C (although Ex-NA-8 showed its propane maximum at 485°C) and for ethylene at 450-460°C. There was also good agreement between the runs in the temperatures at which a weight loss first appeared. Weight loss in all runs except Ex-NA-11 began at 403-404°C. It began at 407°C in Ex-NA-11. This could easily be due to the lower sample size in this run since the balance has a finite sensitivity and the lower sample size could result in a longer lag until the balance was able to detect a change in weight. It should be mentioned here that in all of the runs, some material had appeared in the glass filter located just ahead of the chromatograph at least ten degrees before the balance first showed a loss. After the runs, the residue was put into a Soxhlet extraction apparatus using benzene for solvent for 24 hours. None of the runs taken to completion showed a significant quantity of benzene-soluble material present in the carbonaceous residue.

In addition to the gases mentioned above, a small amount of propylene was observed. Propane, propylene, and ethylene were not analyzed quantitatively since they were present in much smaller amounts than the others. A chromatogram which is typical of those taken during the portion of the run when all of the gases by propylene are present (when propylene is present it appears as a shoulder on the propane peak) is shown in Figure 7. Peak 1 is at an attenuation of 100 x.

Hydrogen, methane, and ethane were identified by means of comparison of retention time with that resulting from injection of a sample containing these compounds in approximately the same composition as that resulting from reaction. Propane and propylene were identified by comparison of retention time with that of pure samples. The difference in retention time between propane and propylene was used to identify ethylene by analogy by comparing the retention time observed for the peak suspected to be ethylene with that for ethane. Peak 1 was found to be hydrogen, peak 2 was methane, peak 3 was ethylene, peak 4 was ethane, peak 5 was propane. These same gases are reported in the literature as products when naphthacene is pyrolyzed at 475°C in a sealed glass ampoule (6). This same reference listed CO and CO₂ as products and there are unidentified peaks between peaks 2 and 3. Water was also given off and was removed from the stream ahead of the chromatograph because it has the same retention time in the column used as does propane.

A chromatogram similar to that which results from chromatography of the condensate after the unreacted naphthacene is removed is shown in Figure 8. The actual resolution which results is much better than that indicated. The only purpose of this figure is to indicate the peaks that result. The order of retention times is read from left to right. The first peak is solvent, the second is an unidentified light compound and the peaks labeled I, II, III, and IV are the ones which were used to obtain quantitative results.

Some of the compounds represented by these peaks were isolated for further study. Compound I appears in the condensate far enough separated from the other components that it was readily available in sufficiently high purity for further analytical work. The sample of it that was obtained showed only one peak in the 1/8-inch column which was used for condensate analysis. Peak II was isolated by means of preparative chromatography. Peaks III and IV were obtained in the same fraction by preparative chromatography and were then separated by hand since the 1/4-inch column used for the preparative work was not capable of resolving these two compounds.

Figure 2 shows the regions in which unreacted naphthacene, compound I, and compound II collect when passing through the condenser. Compounds III and IV collect primarily in the tubing leading from the condenser to the chromatograph and in the glass wool filter at the end of this tubing.

The problem of identification of these compounds proved to be very difficult. The only compound appearing in the condensate which was positively identified besides unreacted naphthacene was 5,12-dihydronaphthacene. The structure of this compound is shown in Table XII. It is reported in the literature as one of the pyrolysis products of naphthacene (5).

A considerable amount of information was obtained to aid in the characterization of compound I. It has a melting point of 145-150°C. The molecular weight measured by Huffman Laboratories by the Rast method indicated that it has the same number of carbon atoms as naphthacene. The result of the carbon and hydrogen determination which was also done by Huffman Laboratories is: carbon, 92.5%; hydrogen, 7.5%. Calculated values for benzyl naphthalene and methyl-benzyl-naphthalene are 6.46 and 6.94% H. The ultraviolet and infrared spectra of this compound are presented in Figures 10 and 11. The infrared appears to be similar to that of a disubstituted naphthalene. It is also quite similar to that for 2-benzyl-naphthalene. The structure of 2-benzyl-naphthalene is shown in Table I. The ultraviolet spectrum also appears to be similar to that of 2-benzyl-naphthalene and calculation of extinction coefficient for this compound indicate two or more fused rings. An attempt was made to run a NMR spectrum of this compound but not enough material was available to get a good spectrum.

Compound II was positively identified as 5,12-dihydronaphthacene. The melting point of compound II was measured in our labora-

tory as 205-210°C. The melting point reported in the literature for 5,12-dihydronaphthacene is 206°C. Huffman Laboratories ran a carbon and a hydrogen determination on compound II and reported 93.55% carbon and 6.22% hydrogen. The calculated value for dihydronaphthacene is 6.08% hydrogen. The molecular weight by the Rast method also agrees with that expected for dihydronaphthacene. The most conclusive evidence, however, comes from infrared spectroscopy. The spectrum for compound II shown in Figure 9 is identical to that reported in the literature for 5,12-dihydronaphthacene (8).

The part of the condensate identified as unreacted naphthacene is identical in appearance, retention time on the chromatograph, and infrared spectrum to that for the starting material.

Some information was obtained about the natures of compounds III and IV. Both compounds appear to have approximately the same molecular weight as naphthacene. Compound III is yellow and sublimes at 241-242°C without leaving a residue. Its infrared and ultraviolet spectra are shown in Figures 12 and 14. The curve marked "C" in Figure 14 is that for compound III. Compound IV is red and sublimes at 260-270°C, leaving a carbonaceous residue. Its infrared and ultraviolet spectra are shown in Figures 13 and 14. The curve marked "B" in Figure 14 is that for compound IV. The column used will not resolve either of these compounds from naphthacene. According to Huffman Laboratories, both of these compounds appear to be esters.

The method of calculation of the stoichiometric coefficients for the gaseous products was mentioned in the previous section. The points which went into the program for integration of gas evolution rate data in order to get the total amount of the gas which had been given off during the run came from smoothed data obtained from the various runs. The results from the different runs were compared in order to determine which points were to be thrown out. From this smoothed data, gas evolution rates, temperature, and amount of weight loss since the beginning of the run was obtained at intervals of one minute. In order to integrate the gas evolution curves it was assumed that the curves were linear over the one-minute intervals.

The method which was used to obtain the stoichiometric coefficients for the solid products is probably not the best method to use, but it was the only one which was capable at all of giving any idea of what the composition of the reaction products was. The first major weakness of the method is that it depends on the manual separation between the 5,12-dihydronaphthacene and the unreacted naphthacene. The reason that it was necessary to make this separation manually is that naphthacene is so much less soluble than the other components of the condensate in the CS_2 used as solvent for the work done with the flame detector, that if the solution contained a representative amount of naphthacene, it would be so dilute in the other components that they would not show up at all due to the tailing of the peaks which becomes very pronounced if the amount of a component in the sample falls below

a certain value. The result of a poor separation between unreacted naphthacene and 5,12-dihydronaphthacene may be seen in Table XI. The sample size in Ex-NA-11 was approximately 25% less than in the other runs which resulted in the amount of condensate being much less. When there was less condensate, it was more difficult to make the separation accurately and evidently some of the 5,12-dihydronaphthacene was included with the unreacted naphthacene, resulting in a calculated conversion to 5,12-dihydronaphthacene that was much lower than that found for other runs. This run was not included in the average values used for the stoichiometric coefficients.

Even if it can be assumed that the manual separation was exact, there is still some weakness in the calculation method itself. Since for a flame ionization detector, peak area is proportional to carbon number and the products found in the condensate have approximately the same molecular weight and contain over 90% carbon, it was assumed that area fraction was proportional to weight fraction. In order to check this assumption, a known amount of 9,10-dimethylantracene was added to a sample of one of the condensates and run through the chromatograph. The sample was 4.44 weight percent dimethylantracene and two samples run through the chromatograph showed 3.54% and 4.06% dimethylantracene by area. This agreement is as close as the certainty with which the weight of the dimethylantracene was known, since the sample only contained 0.2 milligrams of dimethylantracene.

The chief problem with using the chromatograph to do quantitative analysis of this type of compound is that they appear to be adsorbed quite strongly which results in peak broadening and decreased resolution. A silanized support was used to try to reduce this effect, but it was still quite pronounced. If the samples were diluted enough some of the peaks would be broadened enough so that they didn't show at all.

A great deal of the time which was spent on this project was spent in trying to find a gas chromatograph column which would be useful for separating polynuclear aromatic hydrocarbons. The first column that was tried was a fifteen-foot, 1/8-inch diameter column packed with 20% LiCl on Chromosorb W. This column was recommended in the literature (9). For the pyrolysis products of naphthacene, however, it did not work very well. The main problem was that unless it was operated at quite high temperatures, it would adsorb all of the sample, especially naphthacene. When it was operated at sufficiently high temperatures (greater than 300°C), resolution was not very good, retention time was still quite high for naphthacene, and the high temperature was very hard on equipment. The column that was finally used was 5% SE-30 on 50/60 mesh Anakrom ABS. This column could be operated at lower temperatures at lower carrier gas flow rates and still allow all of the sample to come out in thirty minutes. The actual operating conditions that were used were a column temperature of 242°C, injector temperature of 330°C and a nitrogen flow rate of 25 cc/min. The same support and

operating conditions were used in a 1/4-inch column for preparative chromatography. It was also found that the detector temperature could be as low as 200°C without causing flooding of the detector.

The 1/8-inch column used for condensate analysis gave good resolution for all of the products in the condensate except between compounds III, IV, and naphthacene. The 25-foot column did not do any better at this job than did the 15-foot column which was originally tried. The most interesting thing that was discovered while working on the chromatography of the condensate is that if naphthacene is added to the condensate in large quantities, compounds II, III, and IV form one peak. The retention time of compound II is increased and that of III and IV is decreased. It appears that naphthacene may interact strongly with these compounds.

By means of the analytical methods which have been discussed, the stoichiometric equation shown in Table XII was calculated for the overall reactions of naphthacene to 625°C.

The stoichiometric coefficients shown in this equation were obtained by taking the arithmetic mean of the results of Runs 7-10. The value from Ex-NA-10 was not included in the calculation of the coefficient for ethane. The results from Ex-NA-11 were not included because the separation between unreacted naphthacene and 5,12-dihydronaphthacene was not made correctly and because the smaller sample size used for this run appeared to cause some of the differences.

Examination of Table XI and Figures 3-6 shows that there are some significant differences in the quantitative information obtained from the various runs. Before these are discussed, it should be pointed out that the minor differences between the runs in the location of the maxima in gas evolution rates is probably due to variation in heating rate, since this was controlled manually. The same reason would also explain the differences in value of evolution rate at the maximum except for the very large difference in the value of the hydrogen first maximum in Ex-NA-8 as compared to the values of this maximum rate in the other runs. A few possible reasons for this will be mentioned later. For reasons mentioned earlier in this paper, the results from Ex-NA-11 will not be counted. After the stoichiometric coefficients from Run 11 are discounted, there is pretty good agreement between the other runs in the methane coefficients. Comparison of the ethane curve from Ex-NA-10 with that of the other runs shows that its shape is different from that appearing for the others. This difference in shape could be corrected by throwing out the ethane evolution rate at 92 minutes for that run. This would result in an ethane coefficient more in line with that for other runs.

There is a possible explanation for the large hydrogen coefficient for Ex-NA-8 and for the unusually large value for the evolution rate at the maximum. Table XI shows that for this run, more of the naphthacene ended up in the condensate as unreacted naphthacene than in the other runs. The remainder of the condensate was less than

in the other runs. Since the analysis of the condensate indicates that the conversion of naphthacene to these compounds requires hydrogen, it appears that these results are related. A possible explanation might come from the free radical nature of the reactions which occur during pyrolysis. The production of hydrogenated compounds depends on the attack of hydrogen radicals on naphthacene or on some other compound present in the reaction mixture. It might have been possible for something to have been present during this run to cut down on the reactivity of the other compounds to hydrogenation by addition of a hydrogen radical. This would make abstraction of hydrogen from compounds present in the mixture by the hydrogen radicals more likely. Since this would result in more aromatic radicals, a larger conversion to carbonaceous material might be expected. The amount of carbonaceous matter present in the reactor at the end of Ex-NA-8 was greater than in the other runs. There is no real evidence, however, that this is what happened. The preceding discussion is only a possible explanation for what occurred.

Two interrupted runs were made in order to help determine when the compounds present in the condensate were produced. Ex-NA-12 was terminated at 405°C, shortly after the weight loss started. Ex-NA-13 was terminated at 450°C, shortly before the end of the weight loss. The residue from each of these runs was put into a Soxhlet extraction apparatus. The residue from the first run, which amounted to 89.5% of the original sample, contained 68% benzene-soluble material and required only 24 hours for the benzene around the thimble to become clear.

The residue from Ex-NA-12 appeared to contain carbonaceous material, unreacted naphthacene, and a yellow crystalline substance. Chromatography of the residue extract showed the presence of all four peaks labeled in Figure 8. The relative peak areas were similar to those resulting from chromatography of the complete runs except that peak IV was relatively smaller than it appeared in the chromatograms of the complete run condensates. The condensate appeared to contain unreacted naphthacene and a yellow powdery material.

Chromatography of the condensate showed some unidentified light compounds which only appeared because the sample used was much more concentrated than that used for chromatography of the complete run condensates and a large percentage of compound III. No 5,12-dihydronaphthacene appeared to be present.

The residue from Ex-NA-13 was mostly carbonaceous material and contained some unreacted naphthacene. Chromatography of the extract showed the presence of the same compounds as in the previous run. The fraction of compound II appeared to be less in this run than in the previous and peak IV was more pronounced. The condensate from this run looked the same as that from the complete runs. Chromatography of the condensate showed the presence of some compound I, a small amount of compound II, and the remainder was compounds III and IV. There was more compound I present than compound II.

The data obtained in this work agree well with information available in the literature. The boiling point of dihydronaphthacene by

DTA is given as 420°C (5). The same reference shows that naphthacene has a weak exothermic reaction at 480°C which is close to the temperatures at which the evolution rates of methane and ethane had maxima. Dihydronaphthacene did not show up in the 405°C condensate but was present in the 450°C condensate.

From the data obtained from the interrupted runs, the following information about the course of the production of the solid materials present in the condensate may be concluded:

1. All of the compounds which appear in the condensate during the complete runs are first formed at some temperature below 400°C. This evidence indicates that production of these compounds is continuing in the temperature range of 400-450°C. Most of the production of compound IV occurs above 405°C.
2. Compounds I-IV still make up a significant part of the residue at 450°C, although most of the compound I has distilled off by this time.

These results indicate that since one of the major components of the residue that has not already reacted to form carbonaceous matter at 450°C is dihydronaphthacene, it might be possible for some of the non-condensable gases which begin to appear in the temperature range between the two interrupted runs to be formed by cracking of dihydronaphthacene (or of any of the other compounds found in the condensate).

The presence of such a large quantity of oxygenated compounds in the products resulting from the pyrolysis of a hydrocarbon in an inert atmosphere is quite puzzling. This has also occurred in pyrolysis studies appearing in the literature. For example, the gaseous products

of the pyrolysis of naphthacene in a sealed glass ampoule contain 1.5% CO and CO₂ (6). The presence of some oxygenated product is not too surprising since no method is provided for purging the reactor itself at the beginning of the run and polynuclear aromatic hydrocarbons form quinones quite readily. These quinones could undergo further reaction at high temperatures to form other oxygenated materials.

Conclusions

The purpose of this work was to study the reactions occurring during the pyrolysis of naphthacene in order to help obtain a better understanding of how compounds which form a well-ordered graphite react.

Qualitatively, the results obtained from the four complete runs under discussion here agree with each other quite well. It is probable that the first peak in the hydrogen evolution curve is the result of the beginning of a period of rapid removal of hydrogen by reaction to form hydrogenated products. At the end of the runs, the evolution rate of the hydrogen was increasing as cyclodehydrogenation reactions forming graphite-like molecules probably was occurring in the residue. The methane, ethane, ethylene, propane, and propylene which were given off were products of cracking reactions of hydrogenated products formed earlier in the run.

The weight loss curves appear to be caused simply by distillation of products formed earlier in the run and do not reflect what is happening in the reactor at the time during which the loss is taking place.

Table I shows that there was considerable variation in the stoichiometric coefficients obtained from the different runs, so the averages presented elsewhere in this paper should not be regarded as exact values.

There is much room for future work to be done on this compound. Since the weight loss curves provide little information as to the rate at which reactions are occurring, more interrupted runs should be made. At least one run should be made to a temperature below 357°C, the melting point of naphthacene, in order to see whether reactions forming new products occur in the solid phase.

Some hydrogen evolution is evident at these lower temperatures but it could be due to small amounts of residue from previous runs which were not completely cleaned out. It would also be desirable to make a series of interrupted runs with K & K naphthacene and obtain stoichiometric coefficients for a number of intermediate temperatures. More runs should also be made to completion in order to obtain more valid values for the stoichiometric coefficients.

In order to get more information about the oxygenated compounds which were produced, some runs should be made in which a nitrogen purge is provided directly to the interior of the reactor prior to making the run. This would help to show the source of the oxygen.

Appendix

Table I. Compounds Involved in this Work.






<u>Compound</u>	<u>Structure</u>
Naphthacene	
5,12-dihydronaphthacene	
2-benzyl naphthalene	
9,9'-bianthryl	
1,2:11,12-dibenzoperylene	

Table II. Points in Calibration Curves.

<u>Hydrogen</u>		<u>Methane</u>		<u>Ethane</u>	
Peak Ht.	Moles/Min times 10^4	Peak Ht.	Moles/Min times 10^4	Peak Ht.	Moles/Min times 10^4
435	.00488	107	.00492	53.2	.00497
1320	.0194	354	.0196	149.0	.0197
2667	.0391	692	.0394	283.0	.0400
4213	.0780	1063	.0788	473.0	.0801

Table III. Program to Read Calibration Curves.

```

C DATA REDUCTION PROGRAM
  DIMENSION HHT (125), HRT (125), CH4HT(125), CH4RT(125)
  1, C2HT(125), C2RT(125)
  READ 1, HCAL,CCAL,C2CAL,PRESS,NUM
C THESE ARE FROM CALIBRATION DONE ON DAY OF RUN C IS METHANE C2 ETHANE
C NUM IS RUN NUMBER NOW READ CALIBRATION CURVE
  DO 2 I=1,122
    2 READ 3, HHT(I), HRT(I), CH4HT(I),CH4RT(I),C2HT(I),C2RT(I)
C HT IS PEAK HEIGHT RT IS MOLES/MIN*10**4
  3 FORMAT (6F10.0)
  1 FORMAT (4F10.0, I2)
  NOW MAKE CALIBRATION CURVE CORRECTIONS
C CALIBRATION CURVE CORRECTION IS FROM THE L ML LOOP
  CALL TERPOL (CHRT,HHT,HRT,HCAL,122 )
  CORVAL = .218*PRESS/623.4
  HFACT = CORVAL/CHRT
  CALL TERPOL(CCH4RT,CH4HT,CH4RT,CCAL,122 )
  CORVAL = .220*PRESS/623.4
  CFACT = CORVAL/CCH4RT
  CALL TERPOL(C2H6RT, C2HT,C2RT,C2CAL,122)
  CORVAL = .221*PRESS/623.4
  C2FACT = CORVAL/C2H6RT

```

(continued)

Table III (continued)

```

PRINT 6, NUM
6 FORMAT (1H , 20X,6HEX-NA-, 12//)
PRINT 7, HFACT,CFACT,C2FACT
7 FORMAT(1H , 18HCORRECTION FACTORS ,5X,2HH2,F10.3,2X,3HCH4,F10.3,
12X, 4HC2H6,F10.3//)
PRINT 8
8 FORMAT (1H ,8HTIME,MIN ,2X,9HT,DEG. C. ,1X,7HH2 RATE ,3X,
1 8HCH4 RATE ,2X,9HC2H6 RATE )
PRINT 9
9 FORMAT (1H ,23X,24HMOLES/MINUTE TIMES 10**4//)
C TAKE EXPERIMENTAL DATA
DO 50 I=1,60
READ 3,TIME,TEMP,HPKHT,C1PKHT,C2PKHT,GASRT
CALL TERPOL (HRT,HHT,HRT,HPKHT,122)
CALL TERPOL (C1RATE,CH4HT,CH4RT,C1PKHT,122)
CALL TERPOL(C2RATE,C2HT,C2RT,C2PKHT,122)
RTFACT =60./GASRT
C GASRT IS SEC/65CC
HRT = HRT*HFACT*RTFACT
C1RATE = C1RATE*CFACT*RTFACT
C2RATE = C2RATE*C2FACT*RTFACT
PUNCH 51,TIME,TEMP,HRT,C1RATE,C2RATE
50 PRINT 51, TIME,TEMP,HRT,C1RATE,C2RATE
51 FORMAT (1H ,5F10.4 )
CALL EXIT
END

```

This program is Fortran II written for the IBM 1620.

Table IV. Interpolation Subroutine.

```

C      TABLE INTERPOLATION PROGRAM
      SUBROUTINE TERPOL (A,B,C,D,I)
      DIMENSION B(125),C(125)
      IF(D-B(1))18,19,19
19     IF(D-B(I)) 20,33,21
20     IF(D-B(2))26,27,27
26     N=2
      GO TO 23
41     IF(N-I+1) 23,29,29
29     N=N-1
      GO TO 23
27     N=0
22     N=N+1
      IF(D-B(N+1))41,25,22
23     A= C(N-1)*(D-B(N))*(D-B(N+1))*(D-B(N+2))/((B(N-1)-B(N))*(B(N-1)-B(
1N+1))*(B(N-1)-B(N+2))) + C(N)*(D-B(N-1))*(D-B(N+1))*(D-B(N+2))/((
2B(N)-B(N-1))*(B(N)-B(N+1))*(B(N)-B(N+2))) + C(N+1)*(D-B(N-1))*(D-B(
3N))*(D-B(N+2))/((B(N+1)-B(N-1))*(B(N+1)-B(N))*(B(N+1)-B(N+2)))
      A=A+C(N+2)*(D-B(N-1))*(D-B(N))*(D-B(N+1))/((B(N+2)-B(N-1))*(B(N+2
1)-B(N))*(B(N+2)-B(N+1)))

```

(continued)

Table IV (continued)

```
      RETURN
18  A=C(1)
      PRINT 5,D
      5  FORMAT(45H ERROR IN TERPOL,ARGUMENT TOO SMALL FOR TABLE,E12.6)
      RETURN
21  A=C(I)
      PRINT 6,D
      6  FORMAT(45H ERROR IN TERPOL,ARGUMENT TOO LARGE FOR TABLE,E12.6 )
      RETURN
25  A=C(N+1)
      RETURN
33  A=C(I)
      RETURN
      END
```

This program is Fortran II written for the IBM 1620.

Table V. Program for Integration of Gas Evolution Data.

```

C PROGRAM FOR GAS EVOLUTION INTEGRATION AND NORMALIZATION
  READ 1, NUM,SLWT
  SUMH =0.
  SUMC1=0.
  SUMC2=0.
  HRT0=0.
  C1RT0=0.
  C2RT0=0.
  PRINT 4,NUM
  PUNCH 6, NUM
  CARDS = 0.
  DO 50 I=1,500
  READ 2, TIME,TEMP,WTUN,HRT,C1RT,C2RT
  RWT =SLWT-.01105*WTUN
  SLH = HRT/SLWT
  SLC1 =C1RT/SLWT
  SLC2=C2RT/SLWT
  RH = HRT/RWT
  RC1=C1RT/RWT
  RC2=C2RT/RWT
  WTLFR=.01105*WTUN/SLWT
C SL IS RATE NORMALIZATION BASED ON SAMPLE SIZE,R IS BASED ON REACTANT
C PRESENT AT THE TIME
  SUMH = SUMH+(HRT0+HRT)/2.
  SUMC1= SUMC1 +(C1RT0+C1RT)/2.
  SUMC2 = SUMC2+(C2RT0+C2RT)/2.
  SSUMH = SUMH/SLWT
  SSUMC1 =SUMC1/SLWT
  SSUMC2=SUMC2/SLWT
  IF(TIME) 48,48,49
  48 PRINT 8,CARDS
  GO TO 50
  49 PUNCH 7, TIME, TEMP,WTLFR,SLH,SLC1,SLC2,SSUMH,SSUMC1,SSUMC2

```

Table V (continued)

```

PRINT 3,TIME,TEMP,RWT,WTLFR,SLH,RH,SUMH,SSUMH,SLC1,RC1,SUMC1,
1SSUMC1,SLC2,RC2,SUMC2,SSUMC2
PRINT 5
CARDS = CARDS + 1.
HRT0=HRT
C1RT0=C1RT
50 C2RT0=C2RT
1 FORMAT (I2,F8.0)
2 FORMAT (6F10.0)
3 FORMAT (1H ,2F5.0,14F9.4)
4 FORMAT (1H ,60X,6HEX-NA-,I2,17H COMPLETE RESULTS//)
5 FORMAT(5H TIME,6H TEMP ,3X,3HRWT,7X,5HWTLFR,6X,3HSLH,7X,2HRH,5X,
14HSUMH,4X,5HSSUMH, 5X,4HSLC1,6X,3HRC1,4X,5HSUMC1,3X,6HSSUMC1,5X,
24HSLC2,6X,3HRC2,4X,5HSUMC2,3X,6HSSUMC2)
6 FORMAT (34X,6HEX-NA-,I2)
7 FORMAT (2F6.0,7F9.4)
8 FORMAT (1H ,10HTHERE ARE ,F4.0,34H PUNCHED CARDS FOR PLOTTER PROGR
1AM )
C CARD WITH ZEROES IS REQUIRED AT END TO PRINT CARD COUNT
CALL EXIT
END
.      0.      0.      0.      0.      0.

```

-14-

This program is Fortran II written for the IBM 1620.

Table VI. Program to Graph Tables VII-X.

```

C PROGRAM TO MAKE PLOTS
  DIMENSION TIME(200),TEMP(200),WTLFR(200),SLH(200),SLC1(200)
  DIMENSION SLC2(200)
  READ 1,TIMAX,TIMIN,NUM ,NUMB
C NUM IS NUMBER OF DATA CARDS TO BE PLOTTED,TIMIN=TIMAX-200
C NUMB IS RUN NUMBER
  1 FORMAT (2F10.0,2I5)
  DO 10 I=1,NUM
  READ 2, TIME(I),TEMP(I),WTLFR(I),SLH(I),SLC1(I),SLC2(I)
10 WTLFR(I) = -1.* WTLFR(I)
  2 FORMAT (2F6.0, 4F9.4)
  TPMIN = -300.
  TPMAX = 700.
  WMIN = -1.
  WMAX = 0.
  GASMIN = 0.
  GASMAX = .05
  TIMED = 20.
  TEMPD = 100.
  WTLD = .1
  GASD = .005
  XL = 4.5
  YL = 7.
  PUNCH 9,NUMB,TIMIN,TIMAX
  9 FORMAT(6HEX-NA-,I3,6HTIMIN=,F7.0,6HTIMAX=,F7.0)
C PLOT TEMPERATURE

```

(continued)

Table VI (continued)

```

      CALL PLOT(101,TIMIN,TIMAX,XL,TIMED,TPMIN,TPMAX,YL,TEMPD)
      DO 3 I=1,NUM
3     CALL PLOT (9,TIME(I),TEMP(I))
      CALL PLOT(90,TIMIN,TPMIN)
C     PLOT WEIGHT LOSS FRACTION
      CALL PLOT(201,TIMIN,TIMAX,XL,TIMED,WMIN,WMAX,YL,WTLD)
      DO 4 I=1,NUM
4     CALL PLOT(9,TIME(I),WTLFR(I))
      CALL PLOT (90,TIMIN,WMIN)
C     PLOT HYDROGEN,METHANE,ETHANE
      CALL PLOT( 201,TIMIN,TIMAX,XL,TIMED,GASMIN,GASMAX,YL,GASD)
      DO 6 I=1,NUM
6     CALL PLOT (9,TIME(I),SLH(I))
      DO 7 I=1,NUM
7     CALL PLOT(9,TIME(I),SLC1(I))
      DO 8 I=1,NUM
8     CALL PLOT(9,TIME(I),SLC2(I))
      CALL PLOT (90,TIMIN,GASMIN)
      CALL PLOT(99)
      CALL EXIT
      END

```

This program is Fortran II written for the IBM 1620.

Table VII

EX-NA- 7

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2
MIN	DEG C	GM/GM SPLE	MOLES/MIN	GM SPLE*10**4	TOTAL	MOLES/GM SPLE*10**4		
135.	386.	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000
136.	388.	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000
137.	391.	0.0000	.0001	0.0000	0.0000	.0001	0.0000	0.0000
138.	393.	0.0000	.0001	0.0000	0.0000	.0003	0.0000	0.0000
139.	396.	0.0000	.0001	0.0000	0.0000	.0004	0.0000	0.0000
140.	397.	0.0000	.0002	0.0000	0.0000	.0007	0.0000	0.0000
141.	399.	0.0000	.0002	0.0000	0.0000	.0009	0.0000	0.0000
142.	402.	0.0000	.0003	0.0000	0.0000	.0013	0.0000	0.0000
143.	403.	.0020	.0004	0.0000	0.0000	.0016	0.0000	0.0000
144.	405.	.0025	.0004	0.0000	0.0000	.0021	0.0000	0.0000
145.	407.	.0030	.0005	0.0000	0.0000	.0026	0.0000	0.0000
146.	408.	.0040	.0006	0.0000	0.0000	.0032	0.0000	0.0000
147.	408.	.0050	.0007	0.0000	0.0000	.0038	0.0000	0.0000
148.	409.	.0070	.0008	0.0000	0.0000	.0046	0.0000	0.0000
149.	410.	.0100	.0009	0.0000	0.0000	.0054	0.0000	0.0000
150.	411.	.0130	.0010	0.0000	0.0000	.0064	0.0000	0.0000
151.	412.	.0160	.0011	0.0000	0.0000	.0075	0.0000	0.0000
152.	413.	.0201	.0013	0.0000	0.0000	.0088	0.0000	0.0000
153.	413.	.0241	.0015	0.0000	0.0000	.0103	0.0000	0.0000
154.	414.	.0301	.0018	0.0000	0.0000	.0120	0.0000	0.0000
155.	414.	.0372	.0021	0.0000	0.0000	.0140	0.0000	0.0000
156.	414.	.0432	.0022	0.0000	0.0000	.0161	0.0000	0.0000
157.	414.	.0583	.0027	0.0000	0.0000	.0186	0.0000	0.0000
158.	415.	.0704	.0031	.0001	0.0000	.0216	.0001	0.0000
159.	416.	.0814	.0035	.0002	0.0000	.0249	.0003	0.0000
160.	417.	.1025	.0040	.0003	0.0000	.0288	.0006	0.0000
161.	418.	.1408	.0045	.0003	0.0000	.0331	.0009	0.0000

Table VII EX-NA- 7 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL MOLES/GM	SPLE*10**4
162.	420.	.1810	.0050	.0003	0.0000	.0379	.0012	0.0000
163.	421.	.2112	.0064	.0003	0.0000	.0437	.0016	0.0000
164.	422.	.2393	.0102	.0004	0.0000	.0520	.0020	0.0000
165.	424.	.2534	.0102	.0004	0.0000	.0622	.0025	0.0000
166.	426.	.2836	.0101	.0004	0.0000	.0724	.0029	0.0000
167.	428.	.3107	.0095	.0005	0.0000	.0823	.0035	0.0000
168.	431.	.3339	.0090	.0006	0.0000	.0916	.0040	0.0000
169.	433.	.3560	.0086	.0006	0.0000	.1005	.0047	0.0000
170.	436.	.3741	.0083	.0007	0.0000	.1090	.0054	0.0000
171.	438.	.3912	.0078	.0008	0.0000	.1171	.0063	.0001
172.	441.	.4083	.0075	.0009	.0002	.1248	.0072	.0002
173.	444.	.4234	.0071	.0011	.0003	.1321	.0083	.0005
174.	448.	.4395	.0068	.0016	.0004	.1391	.0097	.0010
175.	451.	.4525	.0065	.0023	.0005	.1458	.0117	.0015
176.	454.	.4666	.0062	.0024	.0005	.1522	.0140	.0021
177.	457.	.4757	.0059	.0024	.0006	.1582	.0165	.0027
178.	460.	.4827	.0056	.0025	.0006	.1640	.0190	.0033
179.	462.	.4918	.0053	.0025	.0006	.1695	.0216	.0039
180.	463.	.5028	.0051	.0025	.0006	.1748	.0241	.0046
181.	464.	.5209	.0049	.0026	.0006	.1798	.0268	.0053
182.	465.	.5259	.0049	.0026	.0007	.1848	.0294	.0060
183.	467.	.5259	.0047	.0027	.0007	.1896	.0322	.0067
184.	468.	.5330	.0046	.0028	.0007	.1943	.0350	.0074
185.	469.	.5340	.0045	.0028	.0007	.1990	.0378	.0081
186.	471.	.5350	.0044	.0028	.0007	.2035	.0407	.0088
187.	472.	.5360	.0042	.0029	.0007	.2078	.0436	.0095
188.	473.	.5380	.0040	.0029	.0007	.2120	.0465	.0103

Table VII EX-NA- 7 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
189.	474.	.5400	.0038	.0029	.0007	.2160	.0495	.0110	
190.	475.	.5410	.0035	.0029	.0007	.2197	.0524	.0117	
191.	476.	.5420	.0033	.0029	.0007	.2232	.0553	.0124	
192.	477.	.5430	.0031	.0027	.0006	.2264	.0582	.0131	
193.	478.	.5434	.0028	.0025	.0006	.2294	.0608	.0138	
194.	480.	.5439	.0026	.0024	.0006	.2322	.0634	.0144	
195.	481.	.5443	.0025	.0024	.0005	.2348	.0658	.0150	
196.	482.	.5447	.0023	.0023	.0003	.2372	.0682	.0155	
197.	484.	.5451	.0021	.0023	.0003	.2395	.0706	.0158	
198.	485.	.5471	.0019	.0022	.0002	.2415	.0729	.0161	
199.	487.	.5476	.0018	.0022	.0002	.2435	.0751	.0164	
200.	488.	.5481	.0017	.0021	.0002	.2453	.0773	.0167	
201.	491.	.5484	.0016	.0021	.0002	.2470	.0795	.0169	
202.	493.	.5487	.0016	.0021	.0002	.2487	.0816	.0171	
203.	494.	.5490	.0016	.0021	.0002	.2504	.0838	.0174	
204.	496.	.5493	.0017	.0022	.0002	.2521	.0860	.0176	
205.	500.	.5496	.0018	.0023	.0002	.2539	.0883	.0178	
206.	502.	.5499	.0020	.0024	.0002	.2559	.0907	.0181	
207.	505.	.5502	.0022	.0025	.0002	.2581	.0932	.0183	
208.	508.	.5505	.0026	.0027	.0002	.2605	.0958	.0186	
209.	510.	.5508	.0032	.0029	.0002	.2635	.0987	.0189	
210.	512.	.5511	.0035	.0030	.0002	.2669	.1017	.0192	
211.	514.	.5514	.0036	.0031	.0002	.2705	.1048	.0195	
212.	516.	.5517	.0037	.0032	.0002	.2742	.1080	.0197	
213.	517.	.5520	.0038	.0033	.0002	.2781	.1113	.0200	
214.	518.	.5523	.0039	.0033	.0002	.2820	.1147	.0203	
215.	520.	.5526	.0039	.0033	.0002	.2859	.1181	.0206	

Table VII. EX-NA- 7 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
216.	521.	.5529	.0040	.0033	.0002	.2899	.1215	.0209	
217.	522.	.5532	.0040	.0033	.0002	.2940	.1248	.0211	
218.	523.	.5535	.0040	.0033	.0002	.2980	.1282	.0214	
219.	524.	.5538	.0041	.0033	.0002	.3021	.1315	.0216	
220.	525.	.5541	.0041	.0032	.0001	.3062	.1348	.0218	
221.	526.	.5541	.0041	.0032	.0001	.3104	.1380	.0220	
222.	527.	.5541	.0041	.0031	.0001	.3145	.1412	.0221	
223.	528.	.5541	.0041	.0031	.0001	.3187	.1444	.0223	
224.	530.	.5541	.0042	.0031	0.0000	.3229	.1475	.0224	
225.	532.	.5541	.0042	.0030	0.0000	.3271	.1506	.0224	
226.	533.	.5541	.0037	.0029	0.0000	.3311	.1537	.0225	
227.	535.	.5541	.0031	.0029	0.0000	.3345	.1566	.0226	
228.	536.	.5541	.0024	.0028	0.0000	.3373	.1595	.0226	
229.	538.	.5541	.0016	.0027	0.0000	.3394	.1623	.0226	
230.	539.	.5541	.0014	.0027	0.0000	.3410	.1651	.0227	
231.	541.	.5542	.0015	.0026	0.0000	.3425	.1678	.0227	
232.	542.	.5543	.0019	.0025	0.0000	.3442	.1704	.0227	
233.	544.	.5544	.0023	.0024	0.0000	.3464	.1728	.0227	
234.	547.	.5545	.0025	.0023	0.0000	.3488	.1752	.0227	
235.	548.	.5546	.0026	.0022	0.0000	.3513	.1775	.0228	
236.	550.	.5547	.0026	.0021	0.0000	.3540	.1797	.0228	
237.	552.	.5548	.0027	.0021	0.0000	.3567	.1818	.0228	
238.	553.	.5549	.0027	.0020	0.0000	.3594	.1839	.0228	
239.	554.	.5550	.0028	.0020	0.0000	.3622	.1860	.0228	
240.	556.	.5551	.0028	.0020	0.0000	.3650	.1880	.0228	
241.	558.	.5553	.0028	.0019	0.0000	.3679	.1900	.0228	
242.	560.	.5555	.0028	.0018	0.0000	.3708	.1920	.0228	

Table VII. EX-NA- 7 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
243.	561.	.5557	.0029	.0017	0.0000	.3737	.1938	.0228	
244.	563.	.5559	.0029	.0016	0.0000	.3766	.1955	.0228	
245.	565.	.5561	.0029	.0014	0.0000	.3796	.1971	.0228	
246.	566.	.5563	.0029	.0015	0.0000	.3825	.1986	.0228	
247.	567.	.5565	.0029	.0016	0.0000	.3855	.2002	.0228	
248.	568.	.5567	.0030	.0017	0.0000	.3885	.2019	.0228	
249.	569.	.5569	.0030	.0018	0.0000	.3916	.2037	.0228	
250.	571.	.5571	.0030	.0018	0.0000	.3946	.2056	.0228	
251.	573.	.5571	.0030	.0018	0.0000	.3977	.2074	.0228	
252.	577.	.5571	.0030	.0018	0.0000	.4007	.2093	.0228	
253.	578.	.5571	.0030	.0018	0.0000	.4038	.2111	.0228	
254.	579.	.5571	.0030	.0018	0.0000	.4069	.2130	.0228	
255.	580.	.5571	.0031	.0018	0.0000	.4100	.2148	.0228	
256.	582.	.5571	.0031	.0018	0.0000	.4131	.2167	.0228	
257.	583.	.5571	.0031	.0018	0.0000	.4162	.2185	.0228	
258.	585.	.5571	.0031	.0017	0.0000	.4194	.2203	.0228	
259.	587.	.5571	.0031	.0017	0.0000	.4225	.2221	.0228	
260.	588.	.5571	.0031	.0017	0.0000	.4256	.2238	.0228	
261.	590.	.5572	.0031	.0017	0.0000	.4288	.2256	.0228	
262.	592.	.5573	.0031	.0016	0.0000	.4320	.2273	.0228	
263.	592.	.5574	.0031	.0016	0.0000	.4352	.2290	.0228	
264.	593.	.5575	.0032	.0016	0.0000	.4384	.2306	.0228	
265.	595.	.5576	.0032	.0016	0.0000	.4416	.2323	.0228	
266.	596.	.5577	.0032	.0016	0.0000	.4448	.2340	.0228	
267.	597.	.5578	.0033	.0016	0.0000	.4481	.2356	.0228	
268.	599.	.5579	.0033	.0016	0.0000	.4515	.2373	.0228	
269.	601.	.5580	.0034	.0016	0.0000	.4549	.2390	.0228	

Table VII. EX-NA- 7 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
270.	602.	.5581	.0035	.0016	0.0000	.4584	.2407	.0228	
271.	603.	.5582	.0035	.0016	0.0000	.4619	.2423	.0228	
272.	604.	.5583	.0036	.0016	0.0000	.4655	.2440	.0228	
273.	606.	.5584	.0037	.0016	0.0000	.4692	.2457	.0228	
274.	608.	.5585	.0038	.0016	0.0000	.4730	.2474	.0228	
275.	609.	.5586	.0039	.0016	0.0000	.4769	.2491	.0228	
276.	611.	.5587	.0040	.0016	0.0000	.4809	.2508	.0228	
277.	613.	.5588	.0041	.0017	0.0000	.4850	.2525	.0228	
278.	615.	.5589	.0043	.0017	0.0000	.4893	.2542	.0228	
279.	617.	.5590	.0043	.0017	0.0000	.4936	.2560	.0228	
280.	618.	.5591	.0043	.0017	0.0000	.4980	.2577	.0228	
281.	619.	.5592	.0043	.0017	0.0000	.5023	.2594	.0228	
282.	621.	.5592	.0043	.0017	0.0000	.5067	.2611	.0228	
283.	623.	.5593	.0043	.0016	0.0000	.5110	.2628	.0228	
284.	623.	.5593	.0043	.0016	0.0000	.5154	.2645	.0228	
285.	623.	.5594	.0043	.0016	0.0000	.5197	.2661	.0228	
286.	624.	.5594	.0042	.0016	0.0000	.5240	.2678	.0228	
287.	624.	.5595	.0042	.0015	0.0000	.5283	.2694	.0228	
288.	624.	.5595	.0041	.0015	0.0000	.5325	.2709	.0228	
289.	624.	.5596	.0040	.0015	0.0000	.5366	.2725	.0228	
290.	625.	.5596	.0038	.0014	0.0000	.5406	.2739	.0228	
291.	625.	.5597	.0036	.0014	0.0000	.5443	.2754	.0228	
292.	626.	.5597	.0035	.0014	0.0000	.5479	.2768	.0228	
293.	626.	.5598	.0034	.0013	0.0000	.5514	.2782	.0228	
294.	627.	.5598	.0033	.0013	0.0000	.5548	.2795	.0228	
295.	627.	.5599	.0032	.0012	0.0000	.5580	.2808	.0228	
296.	627.	.5599	.0031	.0012	0.0000	.5612	.2821	.0228	

Table VII. EX-NA- 7 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
297.	627.	.5600	.0030	.0012	0.0000	.5644	.2833	.0228	
298.	628.	.5600	.0030	.0011	0.0000	.5674	.2845	.0228	
299.	628.	.5601	.0029	.0011	0.0000	.5704	.2857	.0228	
300.	629.	.5601	.0028	.0011	0.0000	.5733	.2868	.0228	

This program is Fortran II written for the IBM 1620.

Table VIII

EX-NA- 8

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
92.	401.	0.0000	.0002	0.0000	0.0000	.0001	0.0000	0.0000	
93.	403.	.0010	.0002	0.0000	0.0000	.0003	0.0000	0.0000	
94.	406.	.0020	.0002	0.0000	0.0000	.0005	0.0000	0.0000	
95.	408.	.0025	.0002	0.0000	0.0000	.0007	0.0000	0.0000	
96.	410.	.0030	.0004	0.0000	0.0000	.0011	0.0000	0.0000	
97.	412.	.0072	.0007	0.0000	0.0000	.0016	0.0000	0.0000	
98.	413.	.0103	.0011	0.0000	0.0000	.0026	0.0000	0.0000	
99.	413.	.0185	.0017	0.0000	0.0000	.0040	0.0000	0.0000	
100.	414.	.0237	.0038	0.0000	0.0000	.0068	0.0000	0.0000	
101.	415.	.0361	.0061	0.0000	0.0000	.0117	0.0000	0.0000	
102.	416.	.0505	.0083	.0001	0.0000	.0190	.0001	0.0000	
103.	417.	.0670	.0106	.0002	0.0000	.0285	.0003	0.0000	
104.	418.	.0846	.0129	.0003	0.0000	.0404	.0006	0.0000	
105.	419.	.1093	.0152	.0003	0.0000	.0545	.0010	0.0000	
106.	420.	.1330	.0175	.0004	0.0000	.0709	.0014	0.0000	
107.	421.	.1537	.0198	.0005	0.0000	.0896	.0019	0.0000	
108.	422.	.1743	.0221	.0006	0.0000	.1107	.0025	0.0000	
109.	423.	.2042	.0244	.0007	0.0000	.1340	.0032	0.0000	
110.	425.	.2321	.0245	.0007	0.0000	.1585	.0039	0.0000	
111.	426.	.2620	.0244	.0007	0.0000	.1830	.0047	0.0000	
112.	428.	.2961	.0225	.0007	0.0000	.2065	.0054	0.0000	
113.	429.	.3239	.0206	.0008	0.0000	.2281	.0062	0.0000	
114.	431.	.3476	.0187	.0008	0.0000	.2477	.0071	0.0000	
115.	433.	.3652	.0168	.0008	0.0000	.2655	.0079	0.0000	
116.	435.	.3807	.0156	.0008	0.0000	.2817	.0087	0.0000	
117.	436.	.3951	.0144	.0009	0.0000	.2968	.0096	0.0000	
118.	438.	.4096	.0132	.0009	0.0000	.3107	.0105	0.0000	

Table VIII. EX-NA- 8 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
119.	439.	.4219	.0121	.0010	0.0000	.3234	.0116	.0001	
120.	441.	.4333	.0109	.0011	0.0000	.3349	.0127	.0001	
121.	442.	.4415	.0106	.0012	0.0000	.3457	.0138	.0002	
122.	444.	.4498	.0103	.0013	.0001	.3561	.0151	.0003	
123.	446.	.4580	.0100	.0014	.0001	.3663	.0165	.0004	
124.	448.	.4663	.0097	.0015	.0001	.3762	.0179	.0006	
125.	450.	.4725	.0095	.0016	.0002	.3858	.0195	.0008	
126.	452.	.4776	.0091	.0017	.0002	.3951	.0212	.0011	
127.	453.	.4849	.0086	.0019	.0003	.4041	.0230	.0014	
128.	455.	.4869	.0080	.0020	.0003	.4125	.0250	.0017	
129.	457.	.4931	.0075	.0021	.0004	.4203	.0271	.0022	
130.	460.	.4983	.0071	.0023	.0004	.4276	.0294	.0026	
131.	462.	.5034	.0067	.0024	.0005	.4345	.0317	.0031	
132.	464.	.5055	.0065	.0026	.0006	.4412	.0343	.0037	
133.	466.	.5086	.0064	.0027	.0006	.4477	.0370	.0043	
134.	467.	.5127	.0063	.0029	.0007	.4541	.0399	.0050	
135.	469.	.5138	.0062	.0031	.0007	.4604	.0429	.0058	
136.	471.	.5158	.0061	.0034	.0008	.4666	.0462	.0066	
137.	474.	.5189	.0060	.0035	.0009	.4727	.0497	.0075	
138.	476.	.5210	.0059	.0037	.0009	.4787	.0534	.0085	
139.	478.	.5230	.0058	.0038	.0010	.4846	.0572	.0095	
140.	480.	.5241	.0057	.0038	.0010	.4904	.0610	.0106	
141.	482.	.5272	.0055	.0038	.0011	.4961	.0649	.0117	
142.	483.	.5282	.0053	.0039	.0011	.5016	.0688	.0128	
143.	485.	.5287	.0049	.0039	.0011	.5067	.0727	.0139	
144.	487.	.5292	.0041	.0039	.0011	.5113	.0767	.0151	
145.	488.	.5303	.0036	.0039	.0011	.5151	.0806	.0162	

Table VIII. EX-NA- 8 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL MOLES/GM	SPLE*10**4
146.	489.	.5308	.0032	.0038	.0011	.5186	.0845	.0173
147.	491.	.5323	.0029	.0038	.0010	.5217	.0883	.0184
148.	492.	.5344	.0026	.0037	.0010	.5245	.0921	.0195
149.	492.	.5354	.0023	.0035	.0009	.5270	.0958	.0204
150.	493.	.5365	.0021	.0034	.0008	.5293	.0993	.0213
151.	494.	.5375	.0018	.0032	.0006	.5313	.1026	.0221
152.	496.	.5380	.0015	.0030	.0005	.5330	.1058	.0227
153.	497.	.5390	.0013	.0028	.0002	.5344	.1087	.0231
154.	498.	.5396	.0010	.0027	.0001	.5356	.1116	.0232
155.	499.	.5397	.0009	.0026	0.0000	.5366	.1142	.0233
156.	501.	.5398	.0008	.0024	0.0000	.5375	.1167	.0234
157.	502.	.5399	.0008	.0022	0.0000	.5383	.1191	.0235
158.	503.	.5401	.0009	.0021	0.0000	.5392	.1213	.0236
159.	504.	.5402	.0009	.0020	0.0000	.5402	.1234	.0236
160.	507.	.5403	.0010	.0019	0.0000	.5412	.1255	.0237
161.	509.	.5405	.0010	.0019	0.0000	.5422	.1274	.0238
162.	511.	.5406	.0011	.0019	0.0000	.5433	.1294	.0239
163.	513.	.5406	.0011	.0020	0.0000	.5445	.1314	.0239
164.	514.	.5407	.0011	.0021	0.0000	.5456	.1335	.0240
165.	516.	.5408	.0011	.0021	0.0000	.5468	.1356	.0240
166.	518.	.5408	.0011	.0020	0.0000	.5480	.1377	.0241
167.	519.	.5409	.0011	.0020	0.0000	.5491	.1398	.0241
168.	520.	.5410	.0011	.0019	0.0000	.5502	.1418	.0241
169.	522.	.5410	.0011	.0019	0.0000	.5514	.1437	.0242
170.	524.	.5411	.0010	.0018	0.0000	.5525	.1456	.0242
171.	525.	.5413	.0010	.0018	0.0000	.5536	.1475	.0242
172.	526.	.5414	.0011	.0018	0.0000	.5547	.1493	.0242

Table VIII. EX-NA- 8 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
173.	527.	.5416	.0011	.0017	0.0000	.5558	.1511	.0243	
174.	528.	.5417	.0011	.0017	0.0000	.5569	.1529	.0243	
175.	529.	.5419	.0011	.0017	0.0000	.5580	.1547	.0243	
176.	530.	.5420	.0011	.0017	0.0000	.5591	.1564	.0243	
177.	531.	.5422	.0011	.0016	0.0000	.5603	.1582	.0243	
178.	532.	.5423	.0011	.0016	0.0000	.5614	.1598	.0243	
179.	533.	.5425	.0011	.0015	0.0000	.5626	.1614	.0243	
180.	534.	.5426	.0011	.0015	0.0000	.5637	.1630	.0243	
181.	535.	.5427	.0010	.0015	0.0000	.5649	.1645	.0243	
182.	536.	.5428	.0010	.0015	0.0000	.5659	.1660	.0243	
183.	537.	.5428	.0009	.0015	0.0000	.5669	.1675	.0244	
184.	538.	.5429	.0009	.0015	0.0000	.5679	.1691	.0244	
185.	540.	.5429	.0009	.0015	0.0000	.5689	.1706	.0244	
186.	542.	.5430	.0009	.0015	0.0000	.5698	.1721	.0244	
187.	543.	.5430	.0009	.0015	0.0000	.5707	.1736	.0244	
188.	545.	.5431	.0009	.0015	0.0000	.5717	.1751	.0244	
189.	547.	.5431	.0009	.0015	0.0000	.5726	.1766	.0244	
190.	548.	.5432	.0009	.0015	0.0000	.5736	.1781	.0244	
191.	550.	.5432	.0009	.0015	0.0000	.5745	.1796	.0244	
192.	552.	.5433	.0009	.0015	0.0000	.5755	.1811	.0244	
193.	553.	.5433	.0009	.0015	0.0000	.5765	.1826	.0244	
194.	555.	.5434	.0010	.0015	0.0000	.5775	.1842	.0244	
195.	557.	.5434	.0010	.0015	0.0000	.5785	.1857	.0244	
196.	558.	.5435	.0011	.0015	0.0000	.5796	.1872	.0244	
197.	559.	.5435	.0011	.0015	0.0000	.5807	.1887	.0244	
198.	561.	.5436	.0011	.0015	0.0000	.5819	.1903	.0244	
199.	562.	.5436	.0011	.0015	0.0000	.5830	.1918	.0244	

Table VIII. EX-NA- 8 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
200.	563.	.5437	.0011	.0015	0.0000	.5842	.1933	.0244	
201.	564.	.5437	.0011	.0015	0.0000	.5853	.1948	.0244	
202.	565.	.5438	.0011	.0015	0.0000	.5865	.1963	.0244	
203.	566.	.5438	.0011	.0015	0.0000	.5876	.1979	.0244	
204.	567.	.5439	.0011	.0015	0.0000	.5888	.1994	.0244	
205.	568.	.5439	.0011	.0014	0.0000	.5900	.2009	.0244	
206.	570.	.5440	.0011	.0014	0.0000	.5912	.2024	.0244	
207.	571.	.5440	.0011	.0014	0.0000	.5923	.2039	.0244	
208.	572.	.5441	.0012	.0015	0.0000	.5935	.2054	.0244	
209.	574.	.5441	.0012	.0015	0.0000	.5948	.2069	.0244	
210.	575.	.5442	.0012	.0015	0.0000	.5960	.2084	.0244	
211.	576.	.5442	.0012	.0015	0.0000	.5972	.2099	.0244	
212.	578.	.5443	.0013	.0015	0.0000	.5985	.2114	.0244	
213.	580.	.5444	.0013	.0015	0.0000	.5999	.2130	.0244	
214.	582.	.5444	.0014	.0015	0.0000	.6013	.2145	.0244	
215.	584.	.5445	.0015	.0015	0.0000	.6028	.2161	.0244	
216.	587.	.5445	.0017	.0015	0.0000	.6045	.2176	.0244	
217.	589.	.5446	.0018	.0016	0.0000	.6063	.2193	.0244	
218.	591.	.5446	.0019	.0016	0.0000	.6082	.2209	.0244	
219.	593.	.5447	.0020	.0016	0.0000	.6102	.2226	.0244	
220.	595.	.5447	.0021	.0016	0.0000	.6123	.2242	.0244	
221.	597.	.5448	.0021	.0016	0.0000	.6144	.2259	.0244	
222.	598.	.5448	.0021	.0016	0.0000	.6166	.2276	.0244	
223.	600.	.5449	.0022	.0016	0.0000	.6188	.2293	.0244	
224.	602.	.5449	.0022	.0016	0.0000	.6211	.2310	.0244	
225.	603.	.5450	.0022	.0016	0.0000	.6234	.2327	.0244	
226.	604.	.5450	.0023	.0016	0.0000	.6257	.2344	.0244	

Table VIII. EX-NA- 8 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
227.	606.	.5451	.0023	.0016	0.0000	.6280	.2360	.0244	
228.	607.	.5451	.0024	.0016	0.0000	.6305	.2377	.0244	
229.	609.	.5452	.0024	.0016	0.0000	.6329	.2394	.0244	
230.	611.	.5452	.0025	.0016	0.0000	.6355	.2411	.0244	
231.	612.	.5453	.0026	.0016	0.0000	.6381	.2428	.0244	
232.	614.	.5453	.0026	.0016	0.0000	.6407	.2444	.0244	
233.	616.	.5454	.0027	.0016	0.0000	.6434	.2461	.0244	
234.	618.	.5454	.0028	.0016	0.0000	.6462	.2478	.0244	
235.	619.	.5455	.0028	.0016	0.0000	.6491	.2495	.0244	
236.	622.	.5455	.0029	.0016	0.0000	.6520	.2511	.0244	
237.	623.	.5456	.0029	.0016	0.0000	.6550	.2528	.0244	
238.	623.	.5456	.0030	.0016	0.0000	.6580	.2544	.0244	
239.	624.	.5457	.0030	.0015	0.0000	.6610	.2560	.0244	
240.	625.	.5457	.0030	.0015	0.0000	.6641	.2576	.0244	
241.	626.	.5457	.0030	.0015	0.0000	.6672	.2591	.0244	
242.	627.	.5457	.0030	.0015	0.0000	.6702	.2607	.0244	
243.	627.	.5457	.0029	.0015	0.0000	.6732	.2622	.0244	
244.	627.	.5457	.0029	.0014	0.0000	.6762	.2637	.0244	
245.	628.	.5457	.0028	.0014	0.0000	.6790	.2652	.0244	
246.	628.	.5457	.0027	.0014	0.0000	.6818	.2666	.0244	
247.	629.	.5457	.0026	.0014	0.0000	.6845	.2681	.0244	
248.	630.	.5457	.0025	.0013	0.0000	.6871	.2695	.0244	
249.	630.	.5457	.0024	.0013	0.0000	.6896	.2709	.0244	
250.	630.	.5457	.0024	.0012	0.0000	.6920	.2722	.0244	
251.	630.	.5457	.0023	.0012	0.0000	.6944	.2734	.0244	
252.	630.	.5457	.0023	.0011	0.0000	.6968	.2746	.0244	
253.	631.	.5457	.0022	.0011	0.0000	.6991	.2758	.0244	

Table VIII. EX-NA- 8 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2
MIN	DEG C	GM/GM SPLE	MOLES/MIN	GM SPLE*10**4		TOTAL MOLES/GM	SPLE*10**4	
254.	631.	.5457	.0021	.0011	0.0000	.7013	.2769	.0244
255.	631.	.5457	.0021	.0011	0.0000	.7034	.2780	.0244
256.	632.	.5457	.0020	.0010	0.0000	.7055	.2791	.0244
257.	632.	.5457	.0019	.0010	0.0000	.7075	.2802	.0244
258.	632.	.5457	.0018	.0010	0.0000	.7094	.2812	.0244
259.	633.	.5457	.0017	.0009	0.0000	.7112	.2822	.0244
260.	633.	.5457	.0017	.0009	0.0000	.7130	.2832	.0244

This program is Fortran II written for the IBM 1620.

Table IX

EX-NA-10

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2
MIN	DEG C	GM/GM SPLE	MOLES/MIN	GM SPLE*10**4	TOTAL MOLES/GM SPLE*10**4			
40.	375.	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000
41.	376.	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000
42.	377.	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000
43.	379.	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000
44.	381.	0.0000	0.0000	0.0000	0.0000	.0001	0.0000	0.0000
45.	382.	0.0000	0.0000	0.0000	0.0000	.0001	0.0000	0.0000
46.	384.	0.0000	0.0000	0.0000	0.0000	.0001	0.0000	0.0000
47.	385.	0.0000	0.0000	0.0000	0.0000	.0002	0.0000	0.0000
48.	387.	0.0000	0.0000	0.0000	0.0000	.0002	0.0000	0.0000
49.	388.	0.0000	0.0000	0.0000	0.0000	.0002	0.0000	0.0000
50.	389.	0.0000	0.0000	0.0000	0.0000	.0003	0.0000	0.0000
51.	391.	0.0000	0.0000	0.0000	0.0000	.0003	0.0000	0.0000
52.	392.	0.0000	0.0000	0.0000	0.0000	.0004	0.0000	0.0000
53.	395.	0.0000	0.0000	0.0000	0.0000	.0005	0.0000	0.0000
54.	397.	0.0000	0.0000	0.0000	0.0000	.0006	0.0000	0.0000
55.	399.	0.0000	.0001	0.0000	0.0000	.0007	0.0000	0.0000
56.	400.	0.0000	.0001	0.0000	0.0000	.0008	0.0000	0.0000
57.	402.	0.0000	.0001	0.0000	0.0000	.0009	0.0000	0.0000
58.	403.	0.0000	.0001	0.0000	0.0000	.0011	0.0000	0.0000
59.	404.	.0010	.0001	0.0000	0.0000	.0013	0.0000	0.0000
60.	404.	.0015	.0002	0.0000	0.0000	.0015	0.0000	0.0000
61.	405.	.0030	.0002	0.0000	0.0000	.0017	0.0000	0.0000
62.	406.	.0070	.0003	0.0000	0.0000	.0021	0.0000	0.0000
63.	407.	.0111	.0005	0.0000	0.0000	.0025	0.0000	0.0000
64.	408.	.0161	.0003	0.0000	0.0000	.0030	.0001	0.0000
65.	408.	.0212	.0014	.0001	0.0000	.0039	.0002	0.0000
66.	410.	.0292	.0033	.0001	0.0000	.0062	.0003	0.0000

Table IX. EX-NA-10 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
67.	411.	.0403	.0043	.0002	0.0000	.0100	.0005	0.0000	
68.	413.	.0585	.0057	.0003	0.0000	.0151	.0008	0.0000	
69.	414.	.0767	.0072	.0003	0.0000	.0216	.0012	0.0000	
70.	414.	.0969	.0086	.0003	0.0000	.0295	.0015	0.0000	
71.	415.	.1171	.0094	.0004	0.0000	.0386	.0020	0.0000	
72.	417.	.1403	.0102	.0004	0.0000	.0485	.0024	0.0000	
73.	418.	.1686	.0110	.0004	0.0000	.0592	.0028	0.0000	
74.	421.	.1978	.0119	.0004	0.0000	.0707	.0033	0.0000	
75.	422.	.2261	.0127	.0004	0.0000	.0830	.0037	0.0000	
76.	424.	.2514	.0138	.0004	0.0000	.0963	.0042	0.0000	
77.	427.	.2806	.0150	.0005	0.0000	.1107	.0047	0.0000	
78.	430.	.3049	.0161	.0006	0.0000	.1263	.0053	0.0000	
79.	432.	.3311	.0173	.0008	0.0000	.1430	.0061	0.0000	
80.	434.	.3604	.0173	.0011	0.0000	.1603	.0071	.0001	
81.	437.	.3836	.0173	.0012	.0001	.1776	.0083	.0002	
82.	440.	.4038	.0159	.0016	.0001	.1943	.0097	.0003	
83.	443.	.4180	.0146	.0019	.0002	.2096	.0115	.0005	
84.	447.	.4331	.0133	.0021	.0003	.2236	.0136	.0008	
85.	450.	.4472	.0120	.0023	.0004	.2364	.0159	.0012	
86.	451.	.4583	.0107	.0026	.0006	.2478	.0184	.0017	
87.	454.	.4664	.0107	.0028	.0008	.2586	.0211	.0024	
88.	456.	.4725	.0108	.0030	.0010	.2694	.0240	.0034	
89.	457.	.4785	.0108	.0031	.0013	.2803	.0271	.0046	
90.	458.	.4856	.0110	.0033	.0015	.2913	.0304	.0061	
91.	460.	.4896	.0111	.0035	.0019	.3024	.0339	.0078	
92.	461.	.4937	.0110	.0036	.0020	.3135	.0375	.0098	
93.	461.	.4957	.0108	.0038	.0020	.3244	.0412	.0118	

Table IX. EX-NA-10 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
94.	462.	.4977	.0097	.0039	.0017	.3347	.0452	.0137	
95.	464.	.4997	.0086	.0040	.0015	.3439	.0492	.0153	
96.	466.	.5028	.0075	.0042	.0014	.3520	.0533	.0168	
97.	467.	.5048	.0064	.0043	.0013	.3589	.0576	.0182	
98.	468.	.5078	.0052	.0043	.0011	.3648	.0619	.0194	
99.	469.	.5109	.0042	.0042	.0011	.3696	.0662	.0206	
100.	470.	.5129	.0035	.0041	.0010	.3735	.0705	.0217	
101.	471.	.5149	.0031	.0040	.0009	.3769	.0746	.0226	
102.	473.	.5179	.0029	.0039	.0008	.3799	.0786	.0236	
103.	474.	.5199	.0027	.0038	.0007	.3828	.0826	.0244	
104.	474.	.5209	.0025	.0037	.0007	.3854	.0863	.0252	
105.	475.	.5230	.0024	.0034	.0006	.3879	.0899	.0259	
106.	476.	.5240	.0022	.0033	.0006	.3902	.0933	.0265	
107.	477.	.5260	.0021	.0031	.0005	.3924	.0966	.0271	
108.	478.	.5270	.0019	.0029	.0005	.3945	.0996	.0276	
109.	480.	.5280	.0018	.0028	.0004	.3964	.1025	.0281	
110.	480.	.5310	.0017	.0027	.0004	.3982	.1052	.0285	
111.	480.	.5321	.0016	.0025	.0003	.3999	.1079	.0289	
112.	482.	.5331	.0016	.0025	.0003	.4016	.1104	.0292	
113.	484.	.5341	.0015	.0024	.0002	.4032	.1129	.0295	
114.	486.	.5351	.0014	.0023	.0002	.4047	.1153	.0298	
115.	489.	.5361	.0014	.0022	.0002	.4061	.1176	.0300	
116.	492.	.5371	.0013	.0022	.0001	.4075	.1199	.0302	
117.	493.	.5381	.0013	.0021	.0001	.4089	.1221	.0304	
118.	495.	.5381	.0014	.0021	.0001	.4103	.1243	.0306	
119.	497.	.5381	.0014	.0022	.0001	.4117	.1265	.0307	
120.	498.	.5381	.0014	.0022	.0001	.4132	.1287	.0309	

Table IX. EX-NA-10 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
121.	501.	.5382	.0015	.0022	.0001	.4147	.1309	.0310	
122.	503.	.5383	.0015	.0022	.0001	.4163	.1332	.0312	
123.	504.	.5384	.0015	.0022	.0001	.4178	.1354	.0313	
124.	505.	.5385	.0015	.0022	.0001	.4194	.1377	.0315	
125.	507.	.5386	.0015	.0021	.0001	.4209	.1398	.0316	
126.	510.	.5387	.0015	.0020	.0001	.4225	.1420	.0317	
127.	511.	.5388	.0015	.0020	.0001	.4240	.1440	.0319	
128.	512.	.5389	.0015	.0019	.0001	.4255	.1460	.0320	
129.	513.	.5390	.0014	.0019	.0001	.4270	.1480	.0322	
130.	515.	.5391	.0014	.0019	.0001	.4285	.1500	.0323	
131.	516.	.5392	.0014	.0018	.0001	.4300	.1519	.0325	
132.	517.	.5393	.0014	.0018	0.0000	.4314	.1537	.0326	
133.	519.	.5394	.0013	.0018	0.0000	.4328	.1556	.0326	
134.	520.	.5395	.0013	.0017	0.0000	.4342	.1574	.0327	
135.	521.	.5396	.0013	.0017	0.0000	.4355	.1592	.0327	
136.	522.	.5397	.0013	.0017	0.0000	.4369	.1609	.0327	
137.	523.	.5398	.0013	.0017	0.0000	.4382	.1627	.0327	
138.	524.	.5399	.0012	.0017	0.0000	.4395	.1644	.0327	
139.	526.	.5400	.0012	.0017	0.0000	.4408	.1661	.0327	
140.	526.	.5401	.0012	.0016	0.0000	.4421	.1678	.0327	
141.	527.	.5402	.0012	.0016	0.0000	.4433	.1695	.0327	
144.	534.	.5405	.0011	.0016	0.0000	.4470	.1744	.0327	
145.	535.	.5406	.0011	.0016	0.0000	.4482	.1761	.0327	
146.	537.	.5407	.0012	.0016	0.0000	.4494	.1777	.0327	
147.	538.	.5408	.0012	.0015	0.0000	.4507	.1793	.0327	

Table IX. EX-NA-10 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
148.	541.	.5409	.0013	.0015	0.0000	.4520	.1809	.0327	
149.	543.	.5410	.0013	.0015	0.0000	.4534	.1825	.0327	
150.	544.	.5411	.0014	.0015	0.0000	.4548	.1840	.0327	
151.	546.	.5414	.0014	.0015	0.0000	.4562	.1855	.0327	
152.	547.	.5417	.0014	.0015	0.0000	.4577	.1871	.0327	
153.	548.	.5421	.0015	.0015	0.0000	.4592	.1887	.0327	
154.	550.	.5424	.0015	.0015	0.0000	.4607	.1902	.0327	
155.	551.	.5427	.0015	.0016	0.0000	.4622	.1918	.0327	
156.	553.	.5430	.0015	.0016	0.0000	.4638	.1934	.0327	
157.	554.	.5433	.0015	.0016	0.0000	.4654	.1951	.0327	
158.	556.	.5436	.0016	.0016	0.0000	.4670	.1967	.0327	
159.	557.	.5439	.0016	.0016	0.0000	.4686	.1983	.0327	
160.	558.	.5442	.0016	.0016	0.0000	.4702	.1999	.0327	
161.	559.	.5443	.0016	.0015	0.0000	.4719	.2015	.0327	
162.	560.	.5444	.0016	.0015	0.0000	.4735	.2031	.0327	
163.	561.	.5445	.0016	.0015	0.0000	.4752	.2046	.0327	
164.	562.	.5446	.0016	.0014	0.0000	.4769	.2061	.0327	
165.	563.	.5447	.0017	.0014	0.0000	.4786	.2076	.0327	
166.	563.	.5448	.0017	.0014	0.0000	.4803	.2090	.0327	
167.	565.	.5449	.0017	.0014	0.0000	.4821	.2104	.0327	
168.	567.	.5450	.0017	.0014	0.0000	.4838	.2119	.0327	
169.	569.	.5451	.0017	.0014	0.0000	.4856	.2133	.0327	
170.	570.	.5452	.0017	.0014	0.0000	.4873	.2148	.0327	
171.	571.	.5454	.0018	.0014	0.0000	.4891	.2163	.0327	
172.	573.	.5456	.0018	.0014	0.0000	.4910	.2178	.0327	
173.	575.	.5458	.0019	.0015	0.0000	.4929	.2193	.0327	
174.	576.	.5460	.0020	.0015	0.0000	.4949	.2208	.0327	

Table IX. EX-NA-10 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL MOLES/GM	SPLE*10**4
175.	579.	.5462	.0021	.0015	0.0000	.4970	.2223	.0327
176.	580.	.5464	.0022	.0015	0.0000	.4992	.2238	.0327
177.	583.	.5466	.0024	.0015	0.0000	.5016	.2254	.0327
178.	586.	.5468	.0026	.0016	0.0000	.5041	.2270	.0327
179.	589.	.5470	.0027	.0016	0.0000	.5068	.2286	.0327
180.	591.	.5472	.0029	.0018	0.0000	.5097	.2304	.0327
181.	592.	.5473	.0031	.0019	0.0000	.5127	.2323	.0327
182.	595.	.5475	.0034	.0020	0.0000	.5160	.2343	.0327
183.	598.	.5476	.0037	.0021	0.0000	.5196	.2364	.0327
184.	601.	.5477	.0041	.0021	0.0000	.5236	.2385	.0327
185.	604.	.5479	.0045	.0021	0.0000	.5280	.2407	.0327
186.	607.	.5480	.0049	.0022	0.0000	.5327	.2429	.0327
187.	609.	.5481	.0052	.0022	0.0000	.5378	.2451	.0327
188.	611.	.5483	.0055	.0022	0.0000	.5432	.2474	.0327
189.	614.	.5484	.0058	.0022	0.0000	.5489	.2496	.0327
190.	615.	.5485	.0058	.0022	0.0000	.5548	.2519	.0327
191.	616.	.5487	.0058	.0022	0.0000	.5606	.2541	.0327
192.	617.	.5488	.0057	.0020	0.0000	.5664	.2563	.0327
193.	618.	.5489	.0056	.0020	0.0000	.5721	.2584	.0327
194.	618.	.5491	.0054	.0019	0.0000	.5776	.2603	.0327
195.	619.	.5492	.0051	.0018	0.0000	.5829	.2622	.0327
196.	620.	.5494	.0049	.0018	0.0000	.5880	.2641	.0327
197.	622.	.5495	.0048	.0017	0.0000	.5929	.2659	.0327
198.	622.	.5496	.0047	.0017	0.0000	.5977	.2676	.0327
199.	623.	.5498	.0046	.0016	0.0000	.6024	.2694	.0327
200.	624.	.5499	.0046	.0016	0.0000	.6070	.2710	.0327
201.	625.	.5500	.0045	.0016	0.0000	.6116	.2727	.0327

Table IX. EX-NA-10 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
202.	626.	.5502	.0044	.0015	0.0000	.6160	.2743	.0327	
203.	627.	.5503	.0043	.0015	0.0000	.6204	.2759	.0327	
204.	628.	.5504	.0042	.0013	0.0000	.6247	.2773	.0327	
205.	629.	.5506	.0042	.0014	0.0000	.6290	.2788	.0327	
206.	629.	.5507	.0040	.0014	0.0000	.6331	.2802	.0327	
207.	630.	.5508	.0039	.0014	0.0000	.6372	.2817	.0327	
208.	631.	.5510	.0038	.0014	0.0000	.6411	.2831	.0327	
209.	632.	.5511	.0037	.0013	0.0000	.6449	.2845	.0327	
210.	632.	.5512	.0036	.0013	0.0000	.6487	.2858	.0327	
211.	632.	.5512	.0035	.0013	0.0000	.6522	.2872	.0327	
212.	632.	.5512	.0034	.0012	0.0000	.6557	.2884	.0327	
213.	632.	.5512	.0032	.0012	0.0000	.6591	.2897	.0327	
214.	632.	.5512	.0031	.0011	0.0000	.6623	.2909	.0327	
215.	632.	.5512	.0030	.0011	0.0000	.6653	.2921	.0327	

This program is Fortran II written for the IBM 1620.

Table X
EX-NA-11

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2
MIN	DEG C	GM/GM SPLE	MOLES/MIN	GM SPLE*10**4	TOTAL MOLES/GM SPLE*10**4			
20.	364.	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000
21.	365.	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000	0.0000
22.	365.	0.0000	0.0000	0.0000	0.0000	.0001	0.0000	0.0000
23.	366.	0.0000	0.0000	0.0000	0.0000	.0001	0.0000	0.0000
24.	369.	0.0000	0.0000	0.0000	0.0000	.0001	0.0000	0.0000
25.	373.	0.0000	0.0000	0.0000	0.0000	.0002	0.0000	0.0000
26.	376.	0.0000	0.0000	0.0000	0.0000	.0002	0.0000	0.0000
27.	378.	0.0000	0.0000	0.0000	0.0000	.0003	0.0000	0.0000
28.	381.	0.0000	0.0000	0.0000	0.0000	.0003	0.0000	0.0000
29.	383.	0.0000	0.0000	0.0000	0.0000	.0004	0.0000	0.0000
30.	384.	0.0000	0.0000	0.0000	0.0000	.0004	0.0000	0.0000
31.	386.	0.0000	0.0000	0.0000	0.0000	.0004	0.0000	0.0000
32.	388.	0.0000	0.0000	0.0000	0.0000	.0005	0.0000	0.0000
33.	390.	0.0000	0.0000	0.0000	0.0000	.0005	0.0000	0.0000
34.	392.	0.0000	0.0000	0.0000	0.0000	.0006	0.0000	0.0000
35.	394.	0.0000	0.0000	0.0000	0.0000	.0007	0.0000	0.0000
36.	396.	0.0000	0.0000	0.0000	0.0000	.0007	0.0000	0.0000
37.	398.	0.0000	0.0000	0.0000	0.0000	.0008	0.0000	0.0000
38.	401.	0.0000	0.0000	0.0000	0.0000	.0009	0.0000	0.0000
39.	404.	0.0000	.0001	0.0000	0.0000	.0010	0.0000	0.0000
40.	405.	0.0000	.0001	0.0000	0.0000	.0011	0.0000	0.0000
41.	407.	.0012	.0001	0.0000	0.0000	.0013	0.0000	0.0000
42.	410.	.0032	.0002	0.0000	0.0000	.0015	0.0000	0.0000
43.	412.	.0064	.0003	0.0000	0.0000	.0018	0.0000	0.0000
44.	413.	.0102	.0006	0.0000	0.0000	.0023	0.0000	0.0000
45.	414.	.0205	.0013	0.0000	0.0000	.0033	0.0000	0.0000
46.	415.	.0333	.0030	0.0000	0.0000	.0056	0.0000	0.0000

Table X. EX-NA-11 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2
MIN	DEG C	GM/GM SPLE	MOLES/MIN	GM SPLE*10**4	TOTAL MOLES/GM SPLE*10**4			
47.	416.	.0512	.0047	0.0000	0.0000	.0095	0.0000	0.0000
48.	417.	.0704	.0064	0.0000	0.0000	.0151	.0001	0.0000
49.	417.	.0999	.0081	.0001	0.0000	.0224	.0002	0.0000
50.	417.	.1178	.0098	.0001	0.0000	.0314	.0003	0.0000
51.	419.	.1537	.0115	.0002	0.0000	.0420	.0006	0.0000
52.	421.	.1922	.0131	.0003	0.0000	.0544	.0009	0.0000
53.	423.	.2255	.0148	.0004	0.0000	.0684	.0013	0.0000
54.	425.	.2550	.0165	.0005	0.0000	.0841	.0018	0.0000
55.	426.	.2896	.0182	.0006	0.0000	.1016	.0024	0.0000
56.	427.	.3165	.0187	.0007	0.0000	.1201	.0030	0.0000
57.	430.	.3370	.0189	.0007	0.0000	.1389	.0038	0.0000
58.	433.	.3575	.0191	.0008	0.0000	.1579	.0046	0.0000
59.	435.	.3754	.0191	.0009	0.0000	.1771	.0055	0.0000
60.	436.	.3908	.0192	.0010	0.0000	.1963	.0065	0.0000
61.	439.	.4062	.0191	.0011	0.0000	.2155	.0076	0.0000
62.	441.	.4190	.0190	.0013	0.0000	.2346	.0089	.0001
63.	443.	.4344	.0189	.0015	0.0000	.2537	.0103	.0002
64.	445.	.4510	.0187	.0017	.0001	.2725	.0120	.0003
65.	446.	.4664	.0185	.0019	.0001	.2912	.0138	.0004
66.	448.	.4779	.0181	.0021	.0002	.3095	.0158	.0007
67.	450.	.4882	.0177	.0024	.0003	.3275	.0181	.0009
68.	451.	.4933	.0173	.0027	.0004	.3451	.0208	.0013
69.	453.	.4972	.0168	.0030	.0005	.3622	.0237	.0019
70.	455.	.4997	.0162	.0033	.0007	.3788	.0269	.0025
71.	456.	.5048	.0156	.0035	.0009	.3948	.0303	.0034
72.	457.	.5100	.0149	.0037	.0012	.4101	.0339	.0046
73.	458.	.5125	.0143	.0039	.0015	.4248	.0378	.0059

Table X. EX-NA-11 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
74.	460.	.5151	.0136	.0041	.0016	.4388	.0418	.0075	
75.	461.	.5177	.0130	.0042	.0016	.4521	.0460	.0092	
76.	462.	.5202	.0123	.0044	.0017	.4648	.0503	.0109	
77.	463.	.5228	.0117	.0045	.0017	.4768	.0548	.0126	
78.	464.	.5241	.0110	.0047	.0017	.4882	.0595	.0143	
79.	465.	.5266	.0103	.0048	.0017	.4989	.0643	.0161	
80.	467.	.5279	.0097	.0049	.0017	.5090	.0692	.0178	
81.	468.	.5298	.0090	.0050	.0016	.5184	.0742	.0195	
82.	469.	.5318	.0083	.0050	.0016	.5271	.0793	.0212	
83.	471.	.5343	.0072	.0050	.0016	.5349	.0844	.0228	
84.	473.	.5356	.0061	.0050	.0015	.5416	.0894	.0244	
85.	475.	.5369	.0049	.0049	.0014	.5471	.0944	.0259	
86.	477.	.5382	.0038	.0048	.0013	.5515	.0993	.0273	
87.	478.	.5394	.0026	.0047	.0011	.5547	.1040	.0285	
88.	478.	.5407	.0015	.0046	.0009	.5568	.1087	.0296	
89.	479.	.5414	.0012	.0044	.0008	.5582	.1133	.0305	
90.	482.	.5420	.0011	.0043	.0005	.5594	.1177	.0312	
91.	485.	.5426	.0009	.0041	.0003	.5605	.1219	.0317	
92.	486.	.5433	.0009	.0039	.0002	.5614	.1260	.0320	
93.	488.	.5442	.0008	.0036	.0001	.5623	.1298	.0321	
94.	489.	.5452	.0008	.0032	.0001	.5632	.1332	.0323	
95.	490.	.5462	.0009	.0029	.0001	.5641	.1362	.0324	
96.	492.	.5471	.0011	.0027	.0001	.5651	.1391	.0325	
97.	494.	.5478	.0013	.0025	.0001	.5663	.1417	.0327	
98.	496.	.5484	.0013	.0024	.0002	.5677	.1442	.0329	
99.	499.	.5491	.0013	.0023	.0002	.5691	.1467	.0331	
100.	500.	.5497	.0014	.0022	.0002	.5705	.1490	.0334	

Table X. EX-NA-11 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2
MIN	DEG C	GM/GM SPLE	MOLES/MIN	GM SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4	
101.	502.	.5501	.0014	.0022	.0001	.5719	.1513	.0336
102.	503.	.5505	.0014	.0021	.0001	.5733	.1534	.0337
103.	504.	.5508	.0014	.0020	0.0000	.5747	.1555	.0338
104.	506.	.5512	.0013	.0020	0.0000	.5761	.1575	.0339
105.	508.	.5516	.0013	.0019	0.0000	.5775	.1595	.0340
106.	509.	.5520	.0013	.0019	0.0000	.5788	.1615	.0340
107.	510.	.5524	.0013	.0019	0.0000	.5802	.1635	.0341
108.	512.	.5528	.0013	.0019	0.0000	.5816	.1655	.0341
109.	514.	.5532	.0013	.0019	0.0000	.5830	.1675	.0342
110.	514.	.5535	.0013	.0020	0.0000	.5843	.1695	.0342
111.	516.	.5544	.0013	.0020	0.0000	.5856	.1715	.0343
112.	517.	.5538	.0012	.0020	0.0000	.5869	.1735	.0343
113.	519.	.5539	.0011	.0019	0.0000	.5881	.1755	.0344
114.	520.	.5541	.0010	.0019	0.0000	.5892	.1775	.0344
115.	521.	.5542	.0010	.0019	0.0000	.5903	.1795	.0345
116.	522.	.5543	.0010	.0019	0.0000	.5913	.1815	.0345
117.	524.	.5544	.0010	.0018	0.0000	.5924	.1834	.0346
118.	526.	.5546	.0010	.0018	0.0000	.5934	.1852	.0346
119.	526.	.5547	.0010	.0017	0.0000	.5944	.1870	.0346
120.	527.	.5548	.0010	.0017	0.0000	.5955	.1888	.0346
121.	528.	.5550	.0010	.0016	0.0000	.5965	.1905	.0347
122.	529.	.5552	.0010	.0016	0.0000	.5975	.1922	.0347
123.	531.	.5554	.0010	.0016	0.0000	.5986	.1939	.0347
124.	532.	.5556	.0010	.0016	0.0000	.5996	.1955	.0347
125.	533.	.5558	.0010	.0016	0.0000	.6006	.1972	.0347
126.	534.	.5560	.0010	.0016	0.0000	.6017	.1989	.0347
127.	536.	.5562	.0010	.0016	0.0000	.6027	.2005	.0347

Table X. EX-NA-11 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2
MIN	DEG C	GM/GM SPLE	MOLES/MIN	GM SPLE*10**4	TOTAL MOLES/GM SPLE*10**4			
128.	538.	.5564	.0010	.0016	0.0000	.6038	.2022	.0347
129.	540.	.5566	.0010	.0016	0.0000	.6049	.2039	.0347
130.	541.	.5567	.0011	.0016	0.0000	.6060	.2056	.0347
131.	543.	.5569	.0011	.0016	0.0000	.6071	.2073	.0347
132.	544.	.5571	.0011	.0016	0.0000	.6082	.2090	.0347
133.	546.	.5573	.0011	.0016	0.0000	.6093	.2107	.0347
134.	547.	.5575	.0010	.0016	0.0000	.6104	.2124	.0347
135.	548.	.5577	.0010	.0017	0.0000	.6115	.2141	.0347
136.	549.	.5579	.0011	.0017	0.0000	.6126	.2158	.0347
137.	552.	.5581	.0011	.0017	0.0000	.6138	.2175	.0347
138.	554.	.5583	.0012	.0017	0.0000	.6149	.2192	.0347
139.	556.	.5585	.0012	.0017	0.0000	.6162	.2209	.0347
140.	557.	.5587	.0013	.0017	0.0000	.6175	.2226	.0347
141.	559.	.5587	.0013	.0017	0.0000	.6188	.2243	.0347
142.	561.	.5588	.0013	.0017	0.0000	.6202	.2260	.0347
143.	563.	.5589	.0014	.0017	0.0000	.6216	.2278	.0347
144.	564.	.5589	.0014	.0017	0.0000	.6230	.2295	.0347
145.	565.	.5590	.0014	.0017	0.0000	.6245	.2312	.0347
146.	566.	.5590	.0014	.0017	0.0000	.6259	.2330	.0347
147.	568.	.5591	.0015	.0017	0.0000	.6274	.2347	.0347
148.	571.	.5592	.0015	.0017	0.0000	.6290	.2365	.0347
149.	573.	.5592	.0016	.0017	0.0000	.6306	.2382	.0347
150.	573.	.5593	.0017	.0017	0.0000	.6323	.2400	.0347
151.	574.	.5594	.0017	.0017	0.0000	.6340	.2418	.0347
152.	575.	.5594	.0017	.0017	0.0000	.6357	.2436	.0347
153.	578.	.5595	.0017	.0017	0.0000	.6375	.2454	.0347
154.	582.	.5596	.0017	.0017	0.0000	.6392	.2472	.0347

Table X. EX-NA-11 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPLE	MOLES/MIN	GM	SPLE*10**4	TOTAL	MOLES/GM	SPLE*10**4
155.	584.	.5596	.0017	.0017	0.0000	.6410	.2490	.0347	
156.	586.	.5597	.0017	.0017	0.0000	.6427	.2507	.0347	
157.	586.	.5598	.0018	.0017	0.0000	.6445	.2525	.0347	
158.	586.	.5598	.0018	.0017	0.0000	.6463	.2543	.0347	
159.	586.	.5599	.0018	.0016	0.0000	.6482	.2560	.0347	
160.	587.	.5599	.0019	.0015	0.0000	.6501	.2576	.0347	
161.	588.	.5600	.0019	.0015	0.0000	.6520	.2592	.0347	
162.	589.	.5601	.0019	.0015	0.0000	.6539	.2607	.0347	
163.	590.	.5601	.0019	.0015	0.0000	.6559	.2623	.0347	
164.	591.	.5602	.0019	.0015	0.0000	.6578	.2638	.0347	
165.	592.	.5603	.0019	.0015	0.0000	.6597	.2653	.0347	
166.	593.	.5603	.0019	.0015	0.0000	.6616	.2669	.0347	
167.	594.	.5604	.0019	.0015	0.0000	.6635	.2684	.0347	
168.	597.	.5605	.0019	.0015	0.0000	.6655	.2699	.0347	
169.	598.	.5605	.0019	.0015	0.0000	.6674	.2714	.0347	
170.	600.	.5606	.0019	.0015	0.0000	.6693	.2730	.0347	
171.	601.	.5607	.0019	.0015	0.0000	.6713	.2745	.0347	
172.	602.	.5607	.0020	.0015	0.0000	.6733	.2760	.0347	
173.	604.	.5608	.0020	.0015	0.0000	.6754	.2775	.0347	
174.	607.	.5608	.0020	.0015	0.0000	.6775	.2790	.0347	
175.	607.	.5609	.0021	.0015	0.0000	.6796	.2805	.0347	
176.	608.	.5610	.0021	.0015	0.0000	.6817	.2821	.0347	
177.	610.	.5610	.0022	.0015	0.0000	.6839	.2836	.0347	
178.	611.	.5611	.0022	.0014	0.0000	.6861	.2851	.0347	
179.	612.	.5612	.0023	.0014	0.0000	.6884	.2866	.0347	
180.	614.	.5612	.0023	.0014	0.0000	.6908	.2881	.0347	
181.	614.	.5613	.0023	.0014	0.0000	.6931	.2895	.0347	

Table X. EX-NA-11 (continued)

TIME	TEMP	WTLFR	SLH	SLC1	SLC2	SSUMH	SSUMC1	SSUMC2	
MIN	DEG C	GM/GM	SPL	MOLES/MIN	GM	SPL*10**4	TOTAL	MOLES/GM	SPL*10**4
182.	615.	.5614	.0023	.0014	0.0000	.6955	.2910	.0347	
183.	616.	.5614	.0022	.0014	0.0000	.6978	.2925	.0347	
184.	617.	.5615	.0022	.0014	0.0000	.7000	.2939	.0347	
185.	618.	.5615	.0021	.0013	0.0000	.7022	.2953	.0347	
186.	619.	.5616	.0021	.0013	0.0000	.7044	.2966	.0347	
187.	621.	.5617	.0021	.0012	0.0000	.7066	.2979	.0347	
188.	622.	.5617	.0021	.0012	0.0000	.7087	.2992	.0347	
189.	623.	.5618	.0021	.0012	0.0000	.7109	.3004	.0347	
190.	623.	.5619	.0021	.0012	0.0000	.7130	.3017	.0347	
191.	623.	.5619	.0021	.0012	0.0000	.7152	.3029	.0347	
192.	623.	.5620	.0021	.0012	0.0000	.7173	.3041	.0347	
195.	624.	.5621	.0020	.0012	0.0000	.7194	.3053	.0347	
194.	624.	.5621	.0020	.0012	0.0000	.7215	.3065	.0347	
195.	624.	.5622	.0020	.0012	0.0000	.7235	.3077	.0347	
196.	625.	.5623	.0020	.0011	0.0000	.7256	.3089	.0347	
197.	626.	.5623	.0019	.0011	0.0000	.7276	.3101	.0347	
198.	626.	.5624	.0019	.0010	0.0000	.7296	.3112	.0347	
199.	627.	.5624	.0018	.0010	0.0000	.7315	.3122	.0347	
200.	627.	.5625	.0018	.0009	0.0000	.7334	.3132	.0347	
201.	627.	.5625	.0018	.0009	0.0000	.7352	.3142	.0347	
202.	627.	.5625	.0017	.0009	0.0000	.7370	.3151	.0347	
203.	627.	.5625	.0017	.0008	0.0000	.7388	.3160	.0347	
204.	628.	.5625	.0016	.0008	0.0000	.7405	.3169	.0347	
205.	628.	.5625	.0016	.0008	0.0000	.7422	.3178	.0347	

This program is Fortran II written for the IBM 1620.

Table XI. Results of Individual Runs

Run No.	Residue gm/mol	Unreacted Naphthacene mol/mol	Total Condensate gm/mol	I gm/mol	II mol/mol	III gm/mol	H ₂ mol/mol	CH ₄ mol/mol	C ₂ H ₆ mol/mol
7	98.7	.1928	82.6	3.2	.0556	66.9	.01214	.00616	.000513
8	101.9	.2602	63.7	3.82	.0465	49.2	.0149	.00579	.000548
10	100.0	.1885	81.5	3.26	.0497	68.0	.0140	.00612	.000737
11	98.5	.294	60.5	3.02	.0381	46.6	.0163	.00694	.00078

Table XII. Products of the Pyrolysis of One Mole of Naphthacene

<u>Product</u>	<u>Amount in Moles or Grams</u>	<u>Weight Percent of Original Sample</u>
unreacted naphthacene	.214 moles	21.4
compound I	3.48 grams	1.52
5,12-dihydronaphthacene	.0508 moles	5.12
compounds III and IV	62.3 grams	27.28
carbonaceous residue	102.0 grams	44.66
hydrogen	.0137 moles	.012
methane	.00614 moles	.043
ethane	.00054 moles	.007

Table XIII. Variable Names in the Computer Program

HFACT	pressure correction term for H_2
CFACT	pressure correction term for CH_4
C2FACT	Pressure correction term for C_2H_6
TIME	time recorded during run in order to connect time of sample injection with the continuously measured variables
SL	rate normalization according to sample size -- SLH
R	rate normalization according to material remaining in reactor -- RH
SUM	total amount of gas evolved
SSUM	amount of gas evolved/weight of sample
WTUN	units from the recorder measuring reactor weight
WTLFR	amount of weight lost since the beginning of the run/weight of the sample
XL, YL	length of x and y axes
TIMED	
TEMPD	
WTLD	amount of change in variable value between
GASD	grid lines
MIN, MAX	value of variable at endpoints of the grid

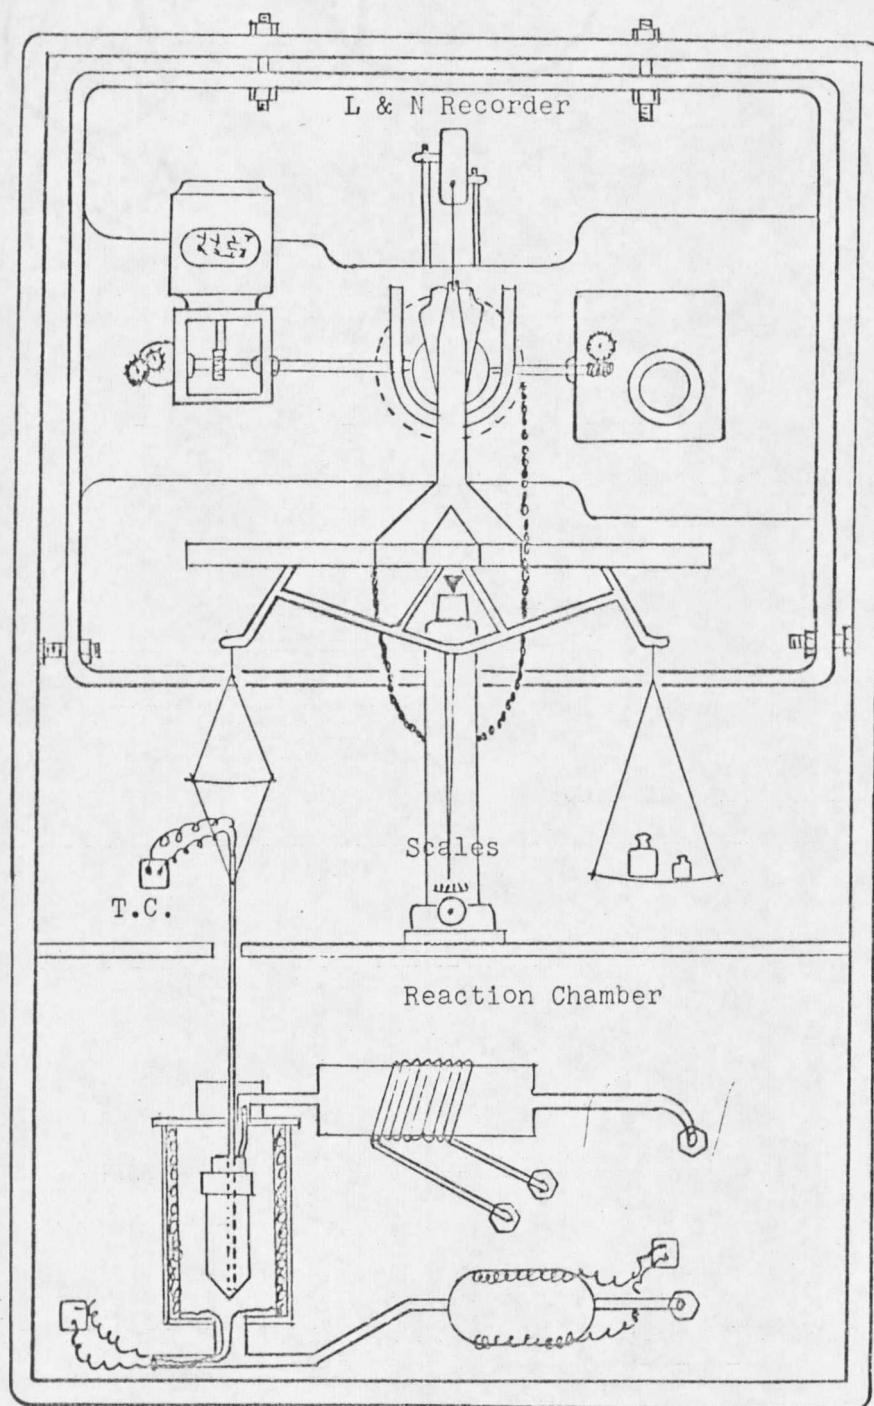


Figure 1. Thermogravimetric Analysis Apparatus

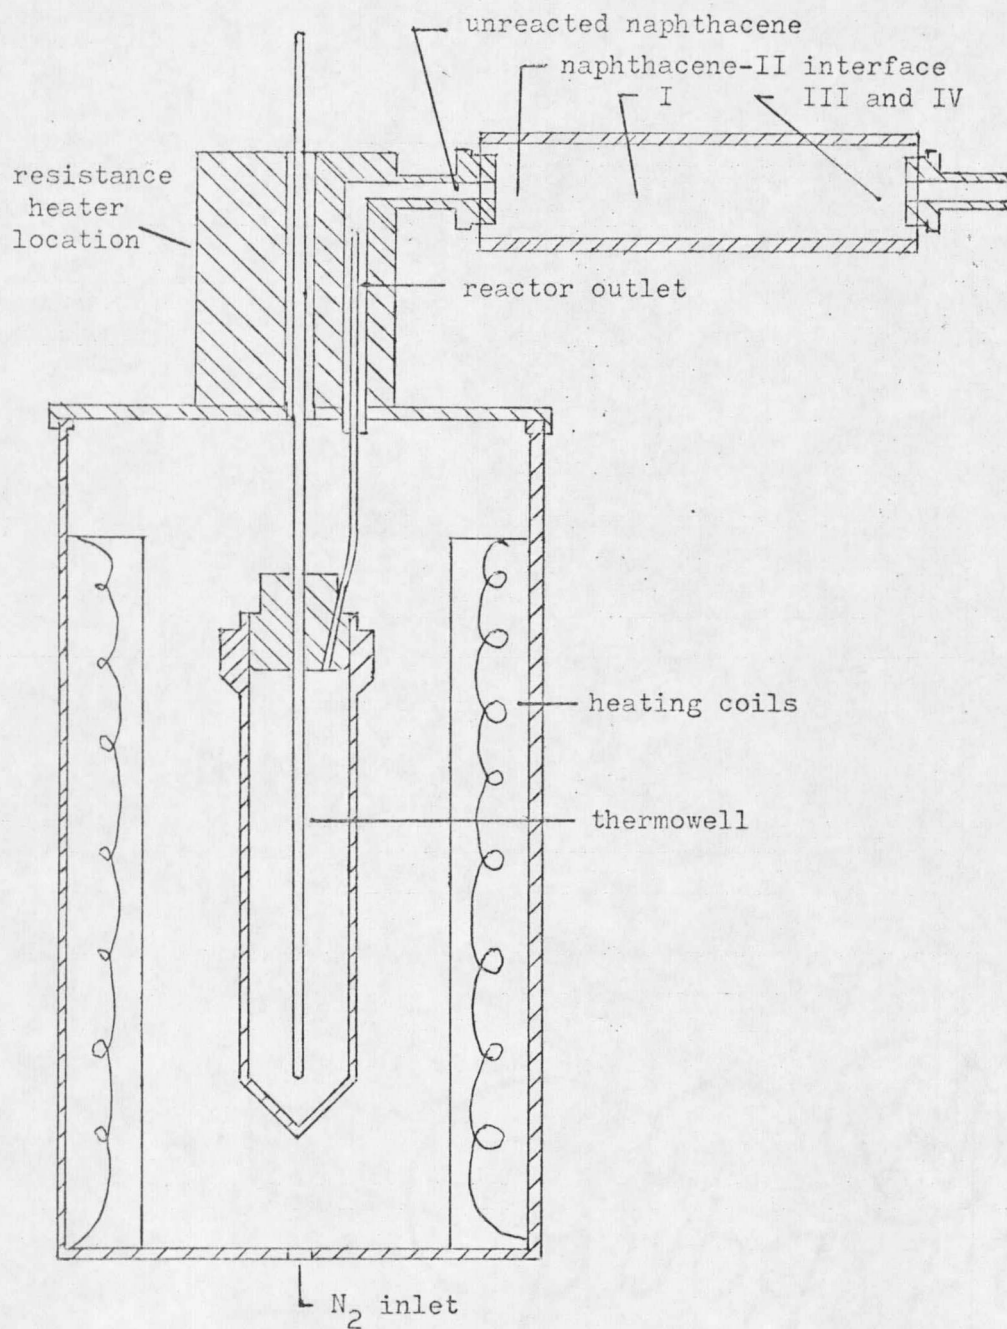


Figure 2. Equipment Modifications and Product Locations

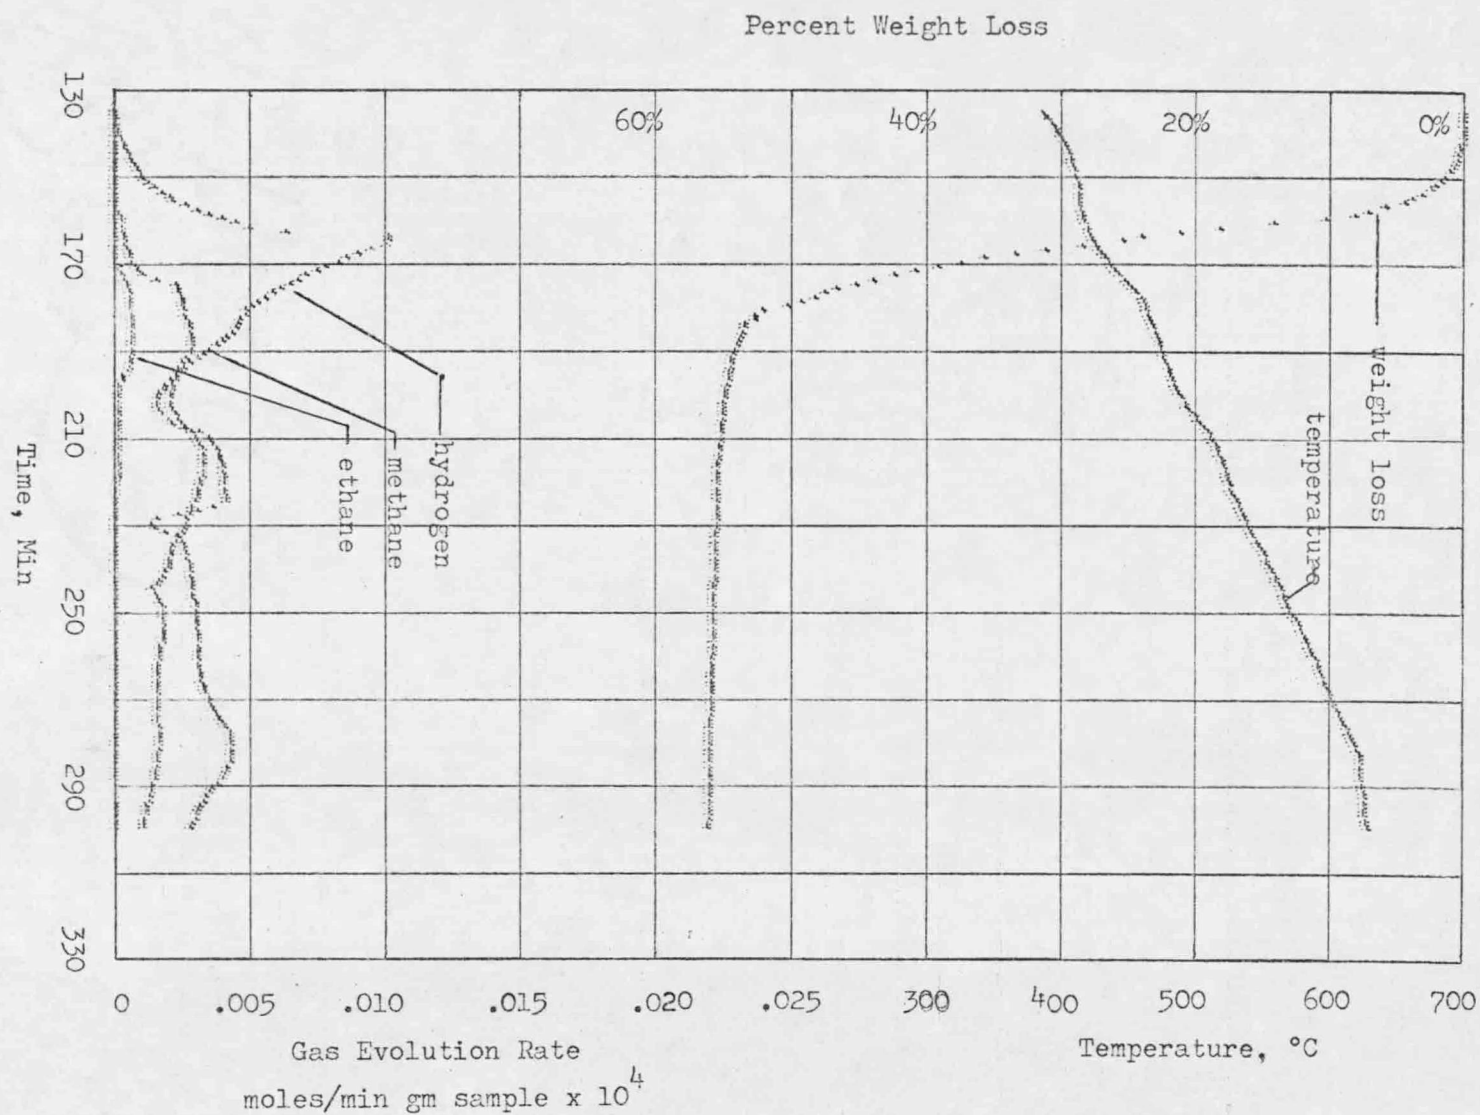


Figure 3. Ex-NA-7 Results.

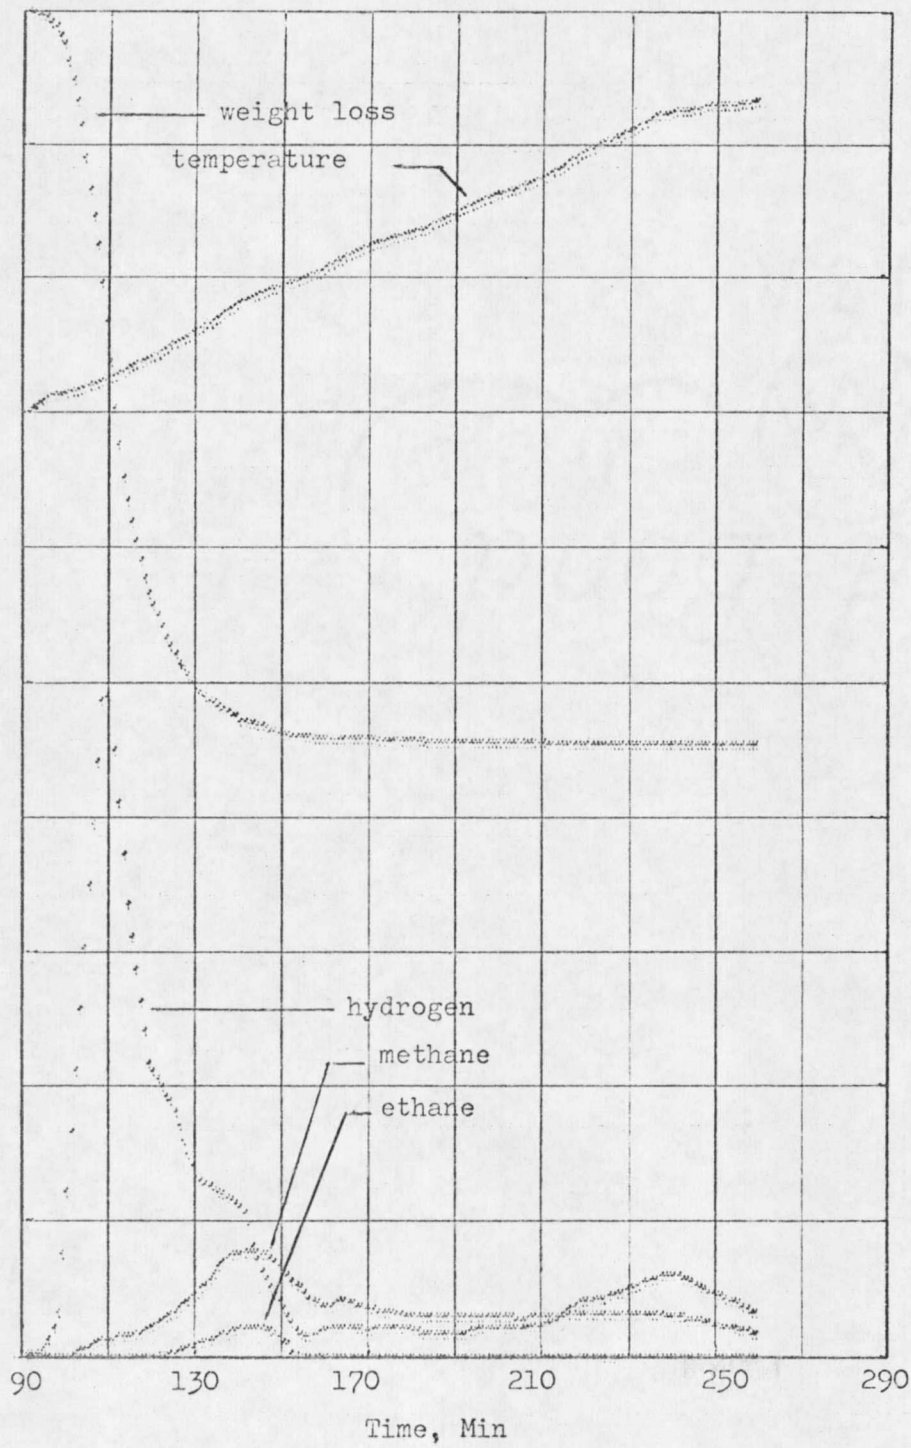


Figure 4. Ex-NA-8 Results.

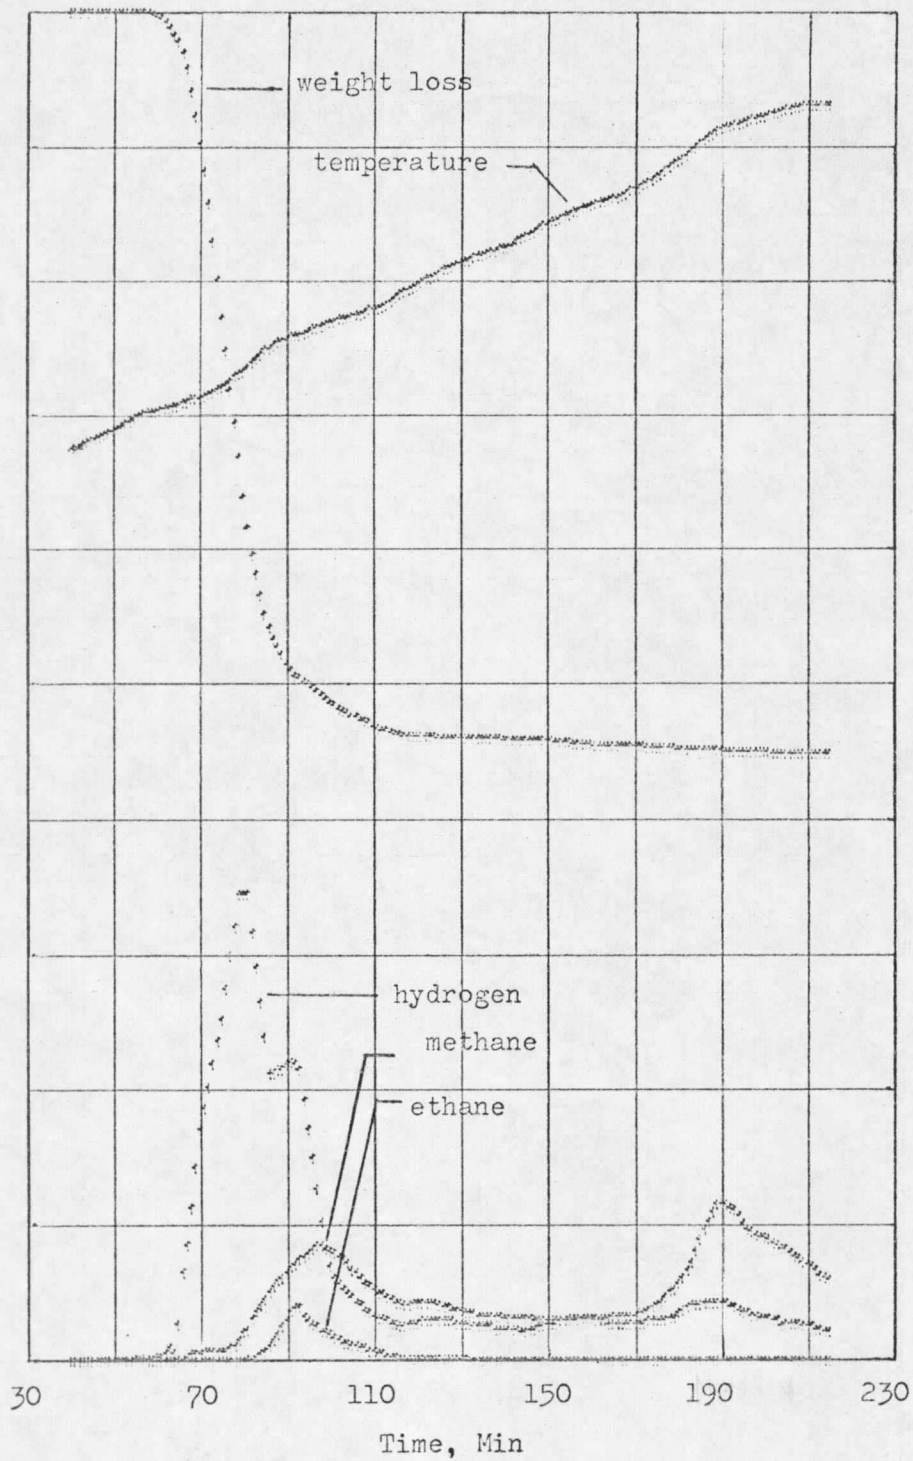


Figure 5. Ex-NA-10 Results.

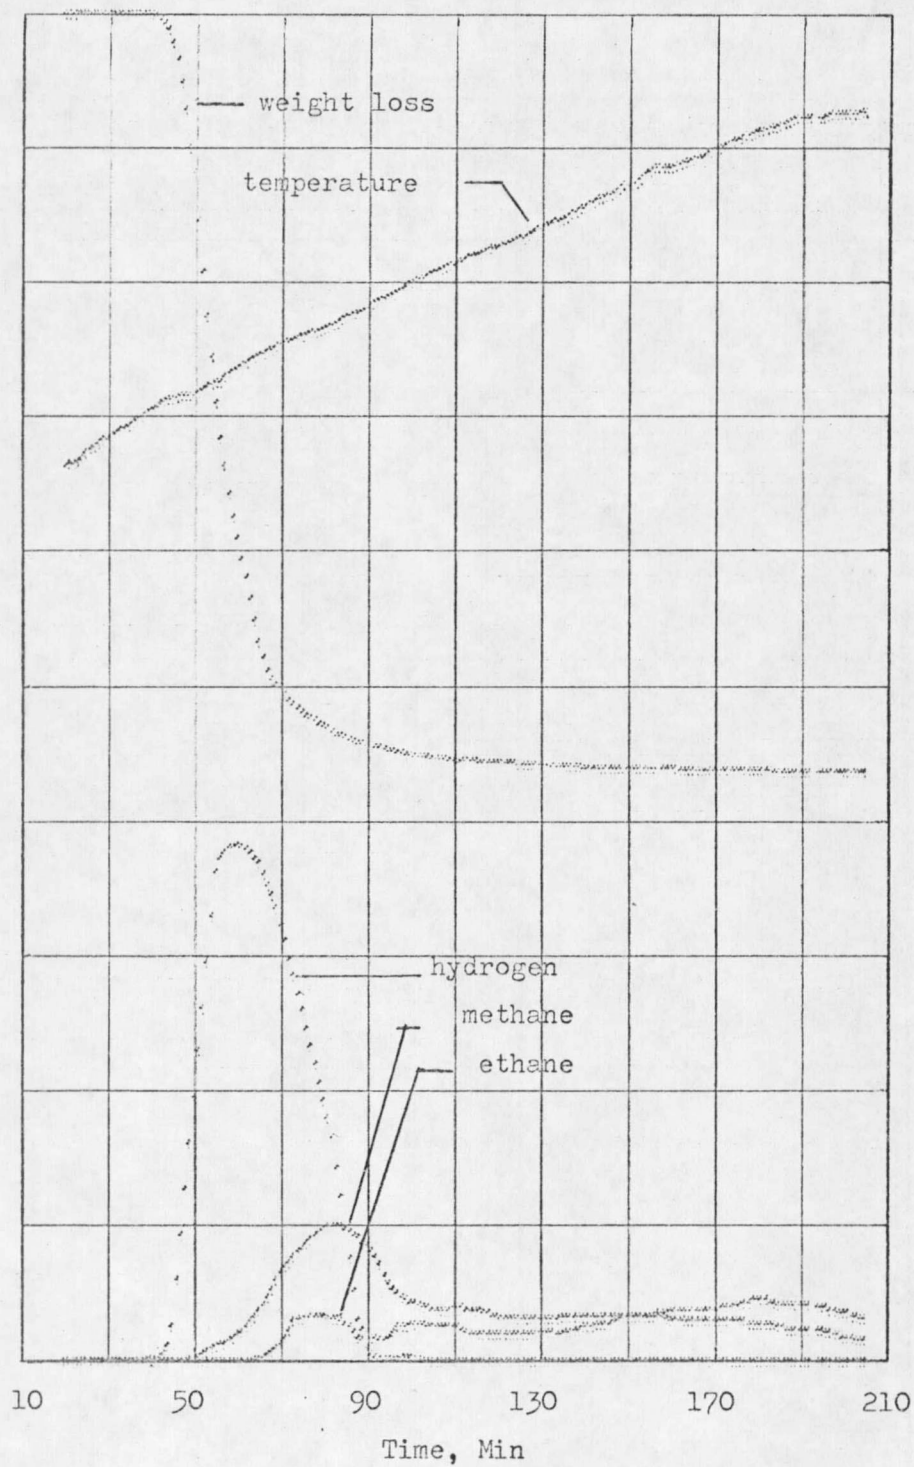


Figure 6. Ex-NA-11 Results.

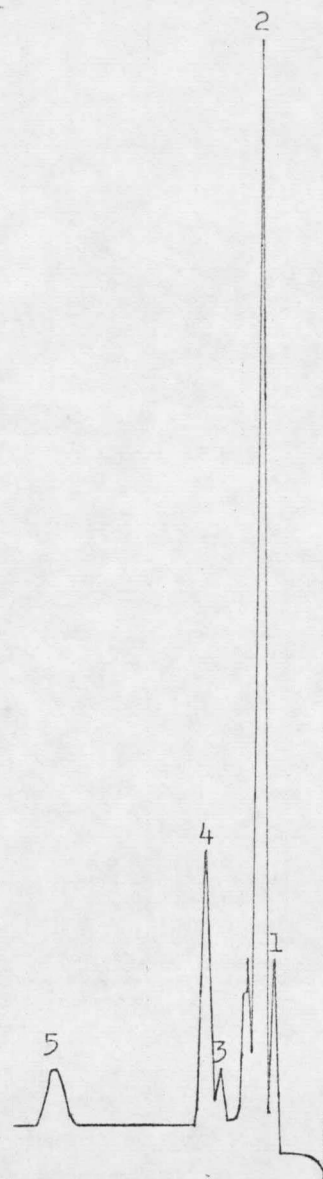


Figure 7. Chromatogram of Gaseous Products.

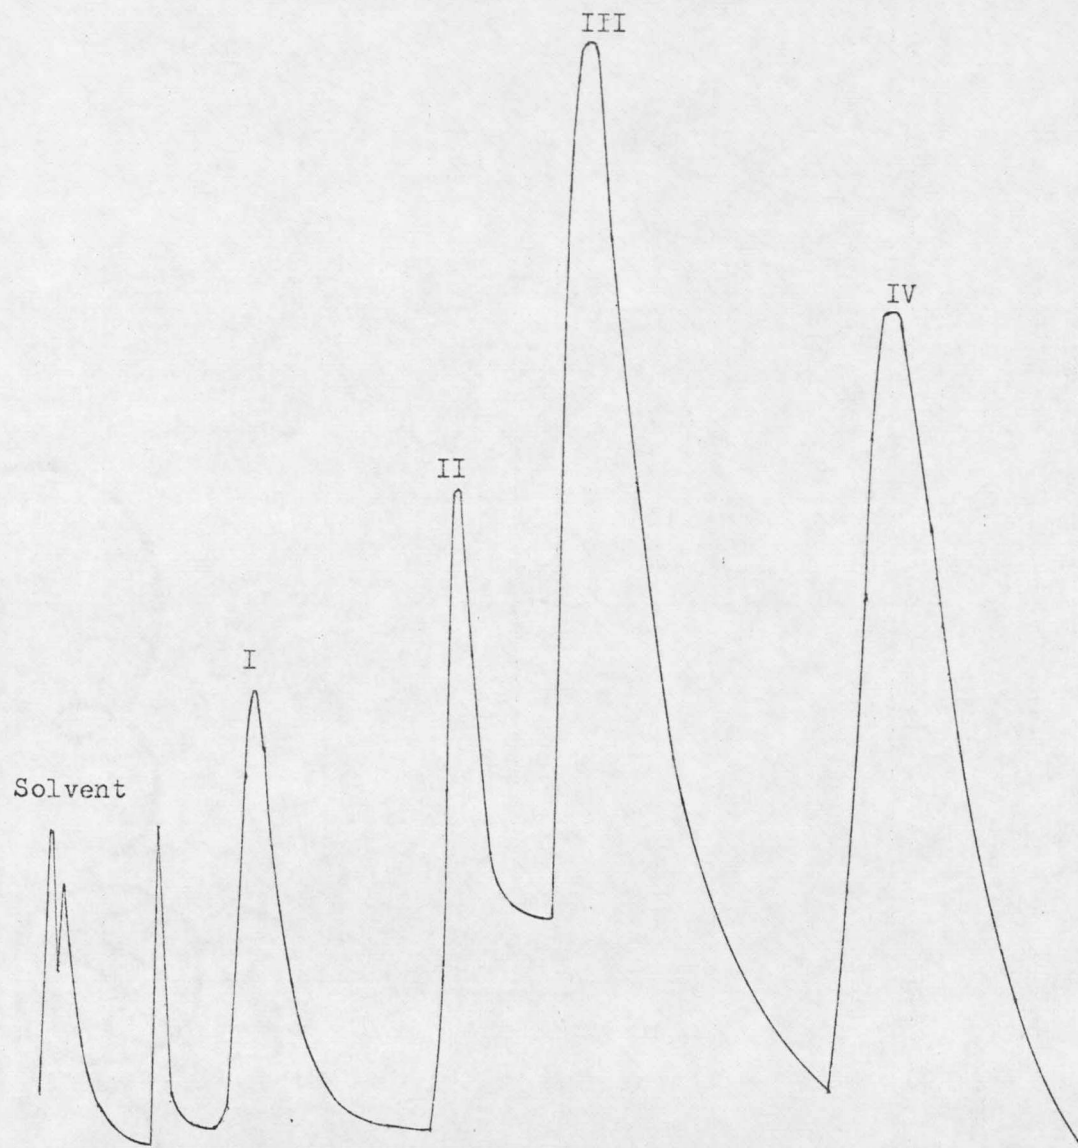


Figure 8. Condensate Chromatogram.

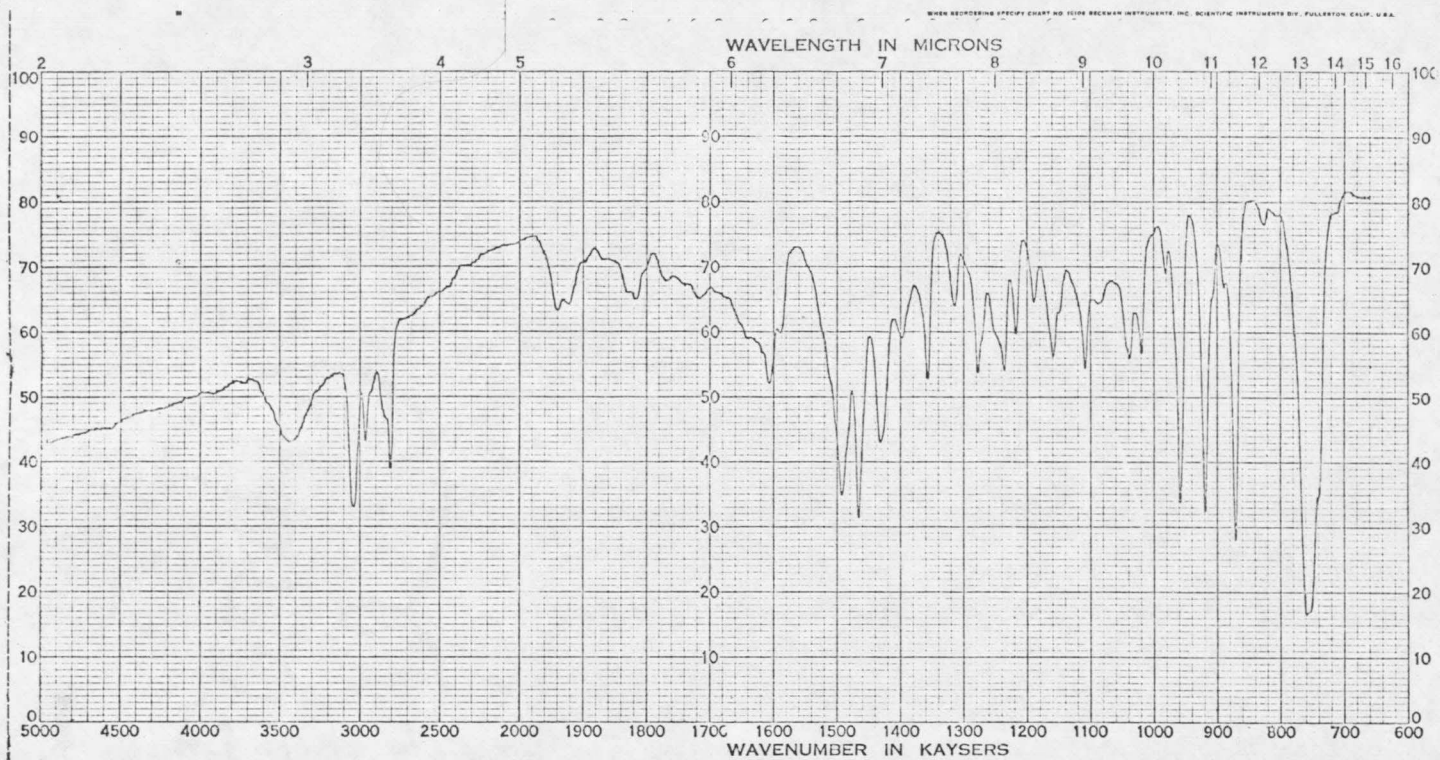


Figure 9. Infrared Spectrum of Compound II.

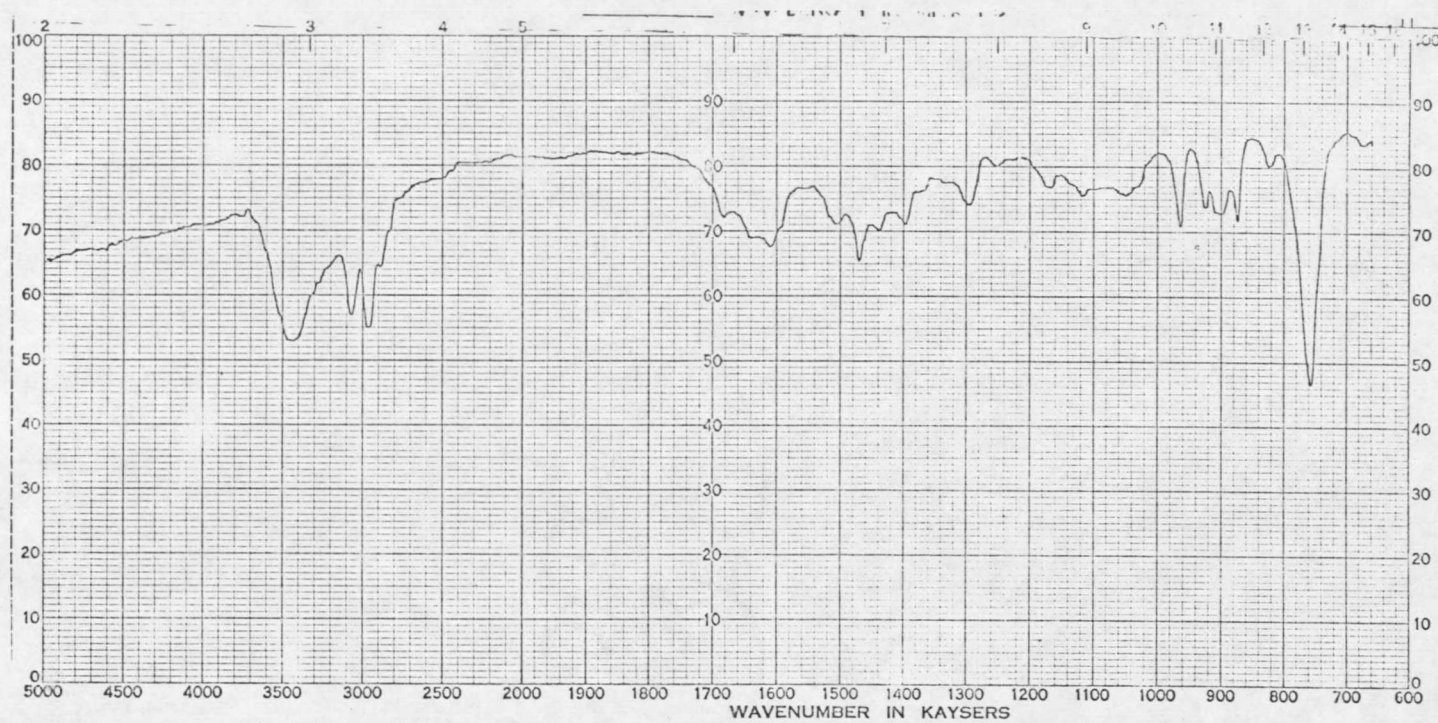


Figure 10. Infrared Spectrum of Compound I.

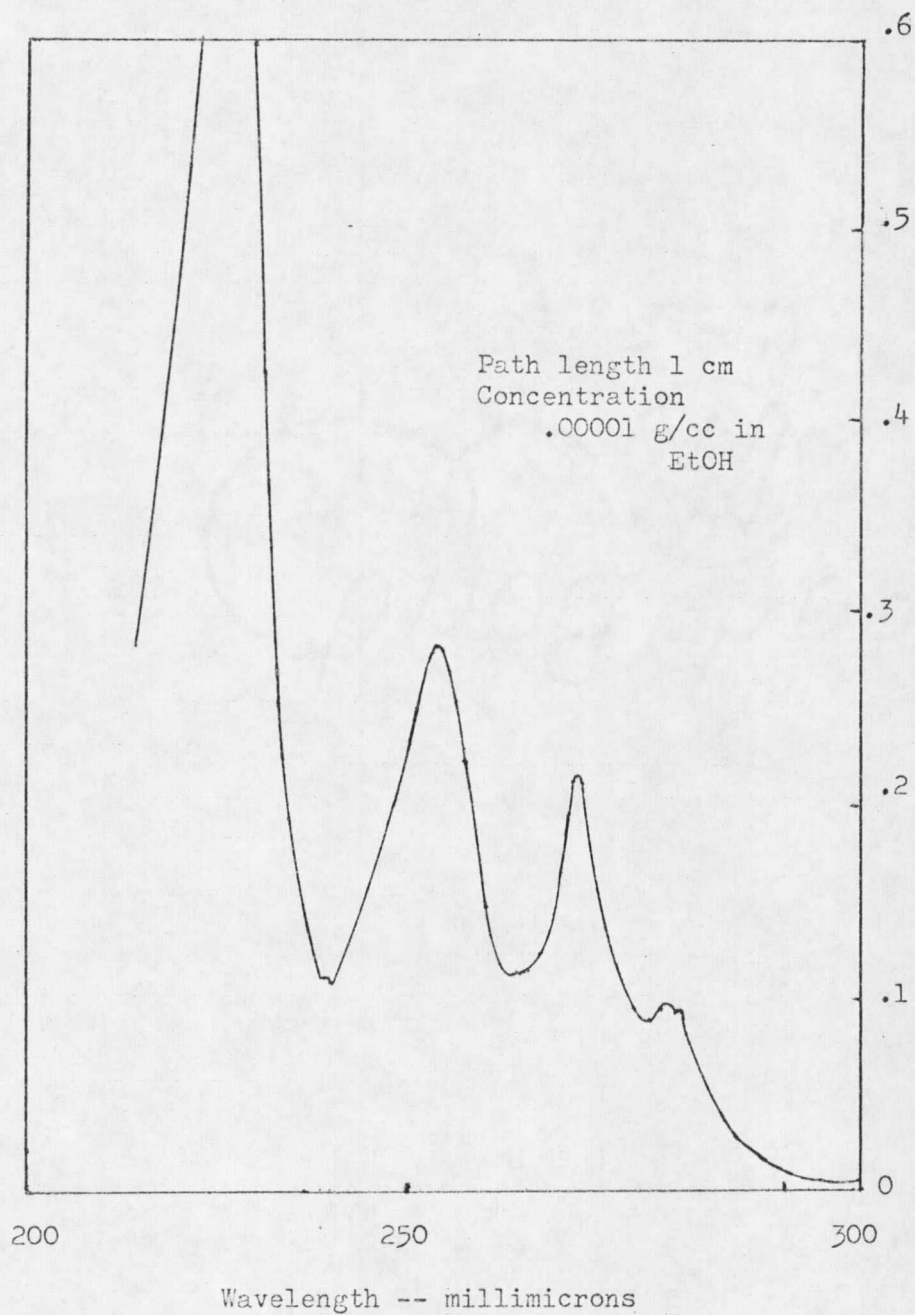


Figure 11. Ultraviolet Spectrum of Compound I.

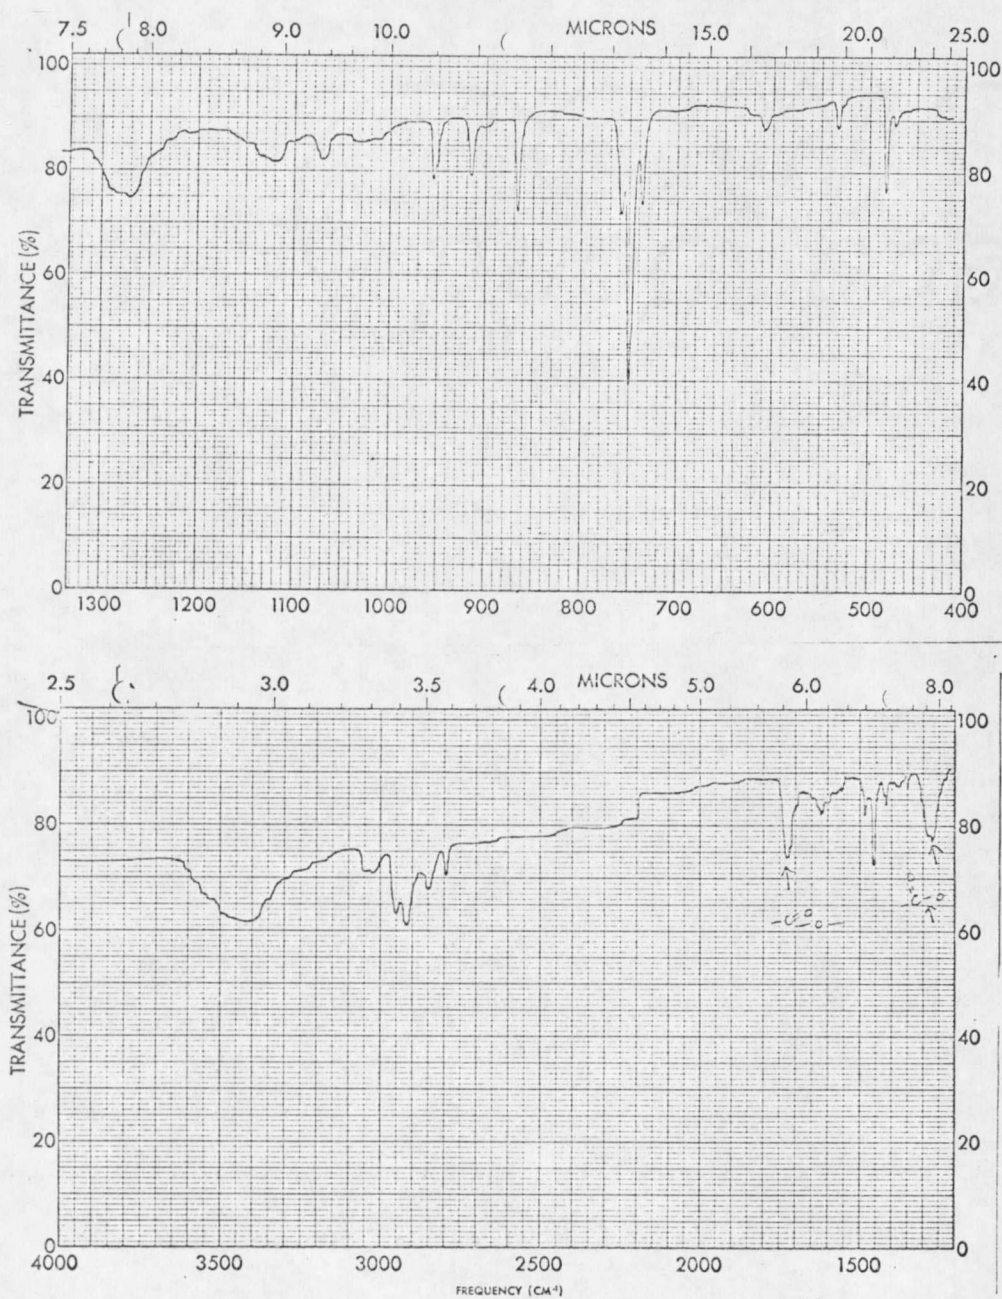


Figure 12. Infrared Spectrum of Compound III.

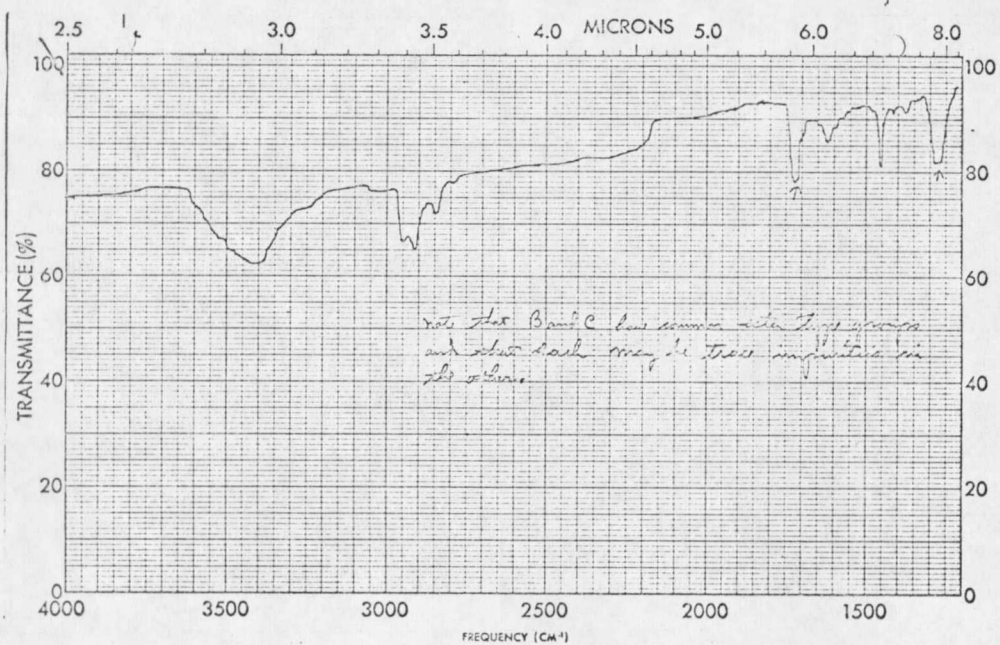
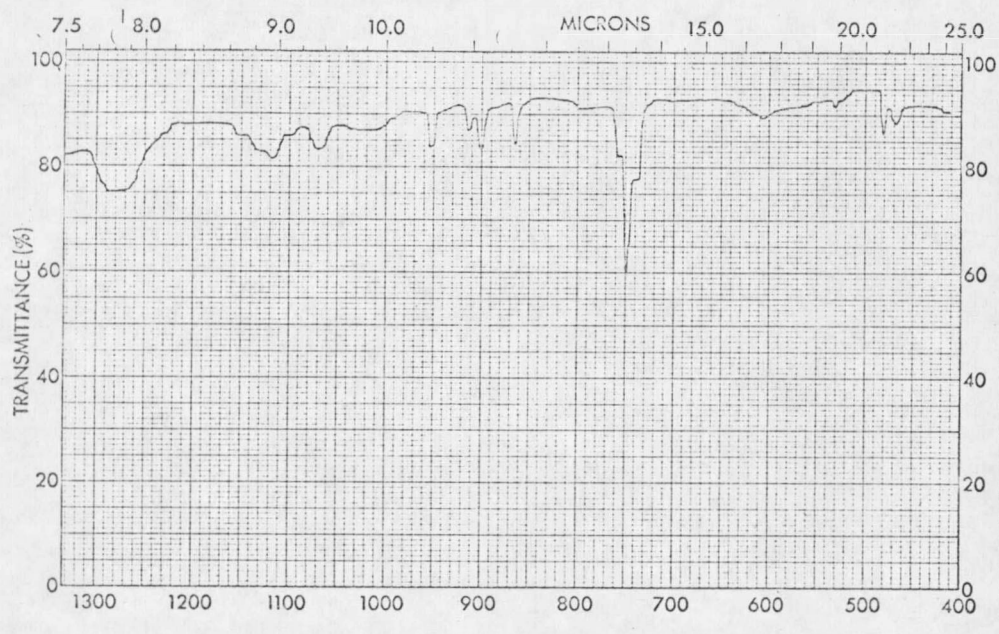


Figure 13. Infrared Spectrum of Compound IV.

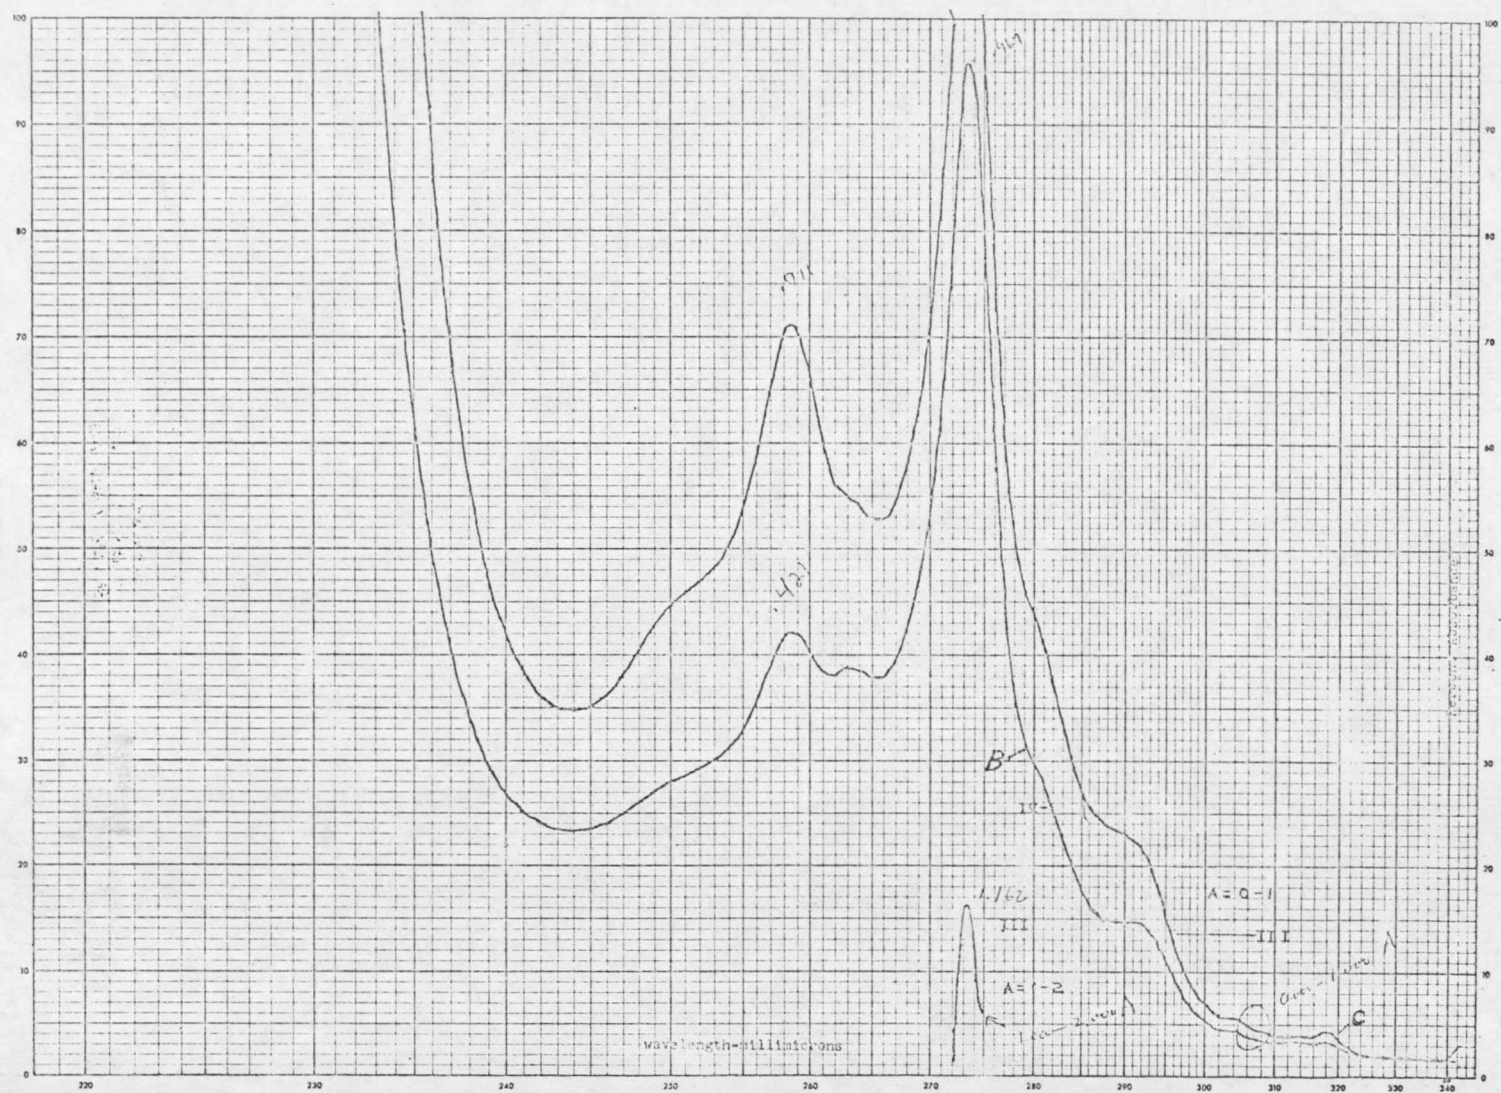


Figure 14. Ultraviolet Spectra of Compounds III and IV in Ethanol.

Literature Cited

1. Bushong, R. M., et. al. Improved Graphite Materials for High Temperature Aerospace Use. Volume I. Research and Development for Improved Graphite Materials. Technical Documentary Report No. ML-TDR-64-125 Air Force Materials Laboratory Research, Patterson Air Force Base, Ohio (1964) pp. 41-43.
2. Brooks, J. D., and Taylor, G. H. "The Formation of Graphitizing Carbons from the Liquid Phase." Carbon, 3 (1965), 185.
3. Badger, G. M., Donnelly, Jillian K., and Spotswood, T. M. "The Formation of Aromatic Hydrocarbons at High Temperatures XXIII. The Pyrolysis of Anthracene." Australian Journal of Chemistry, 17 (1964), 1147-1156.
4. Personal Communication, Dr. J. R. Kiovsy, Continental Oil Company, 1966.
5. Lewis, Irwin C., and Edstrom, T. "Thermal Reactivity of Polynuclear Aromatic Hydrocarbons." Journal of Organic Chemistry, 28 (1963), 2050-2054.
6. Madison, John J., and Roberts, Richard M. "Pyrolysis of Aromatics and Related Heterocyclics." Industrial and Engineering Chemistry, 50 (1958), 242.
7. Currie, Robert A. A Kinetic Study of the Pyrolysis Reactions of Acenaphthylene and Bifluorenyl. Ph.D. thesis, Montana State University, Bozeman, Montana, 1966.
8. Infrared Spectral Data of American Petroleum Institute Research Project 44, Serial No. 2230.
9. Guvernator, C., et. al. "Electron Capture Detection of Gas-Chromatographed Polycyclic Hydrocarbons." Journal of Gas Chromatography, 3 (1965), 363-367.

MONTANA STATE UNIVERSITY LIBRARIES



3 1762 10015188 3

N378
P537
cop.2

Philip, J. C.
The pyrolysis of naphthacene.

NAME AND ADDRESS

N378
P537
cop.2

